

**RESERVES AND RESOURCES IN THE SAN MARTIN MINE,
QUERETARO STATE, MÉXICO
AS OF APRIL 30, 2018**

UTM Nad 27 México Coordinates
Centered at approximately:
(398,300E and 2,292,500N)



Prepared for:
STARCORE INTERNATIONAL MINES LTD.



Prepared by:
Erme Enriquez C.P.G., BSc, MSc
Effective date: April 30, 2018
Report date: June 27, 2018

TABLE OF CONTENTS

1. SUMMARY.....	7
1.1 Introduction.....	7
1.2 Property Description and Location	7
1.3 Exploration and Mining History	7
1.4 Gold and Silver Processing and Recovering.....	8
1.5 Geology and Mineralization	8
1.6 Mineral Resources Estimate	8
1.7 Mineral Reserve Estimate	11
1.8 Mining Operations	11
1.9 Conclusions and Recommendations	12
2. INTRODUCTION.....	14
2.1 Issuer and Terms of Reference	14
2.2 Source of Information.....	14
2.3 Qualified Person	15
2.4 Units and Currency	15
3. RELIANCE ON OTHER EXPERTS.....	15
4. PROPERTY DESCRIPTION AND LOCATION.....	16
4.1 Location	16
4.2 Property Description	17
4.3 Mineral Tenure, Agreements and Encumbrances.....	19
5. ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY	19
5.1 Access	19
5.2 Climate.....	20
5.3 Local Resources and Infrastructure	20
5.4 Physiography	21
6. HISTORY	22
7. GEOLOGICAL SETTING AND MINERALIZATION	23
7.1 Geology.....	23
7.2 Mineralisation	24
8. DEPOSIT TYPE.....	27
9. EXPLORATION	28
10. DRILLING.....	29
11. SAMPLE PREPARATION, ANALYSES AND SECURITY	30
12. DATA VERIFICATION.....	31
13. MINERAL PROCESSING AND METALLURGICAL TESTING.....	32
13.1 Process of the Benefit Plant	32
14. MINERAL RESOURCE ESTIMATES	35
14.1 Introduction.....	35
14.2 Density	35
14.3 Methodology	35

15.0 MINERAL RESERVE ESTIMATES	37
15.1 Introduction.....	37
15.2 Methodology.....	38
15.3 Definitions	39
15.4 Reconciliation of Mineral Reserves to Production	42
15.5 Mineral Reserves	43
15.6 Factors that may affect the Reserve Calculation	45
16. MINING METHODS	47
16.1 Mining Operations	47
16.2 Mining Method	47
16.3 Mining Equipment	52
17. RECOVERY METHODS	53
18. PROJECT INFRASTRUCTURE	53
19. MARKET STUDIES AND CONTRACTS	55
20. ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT	55
20.1 General.....	55
20.2 Permitting.....	55
20.3 Tailings Dam and Reforestation	56
20.3 Social and Community Impact	57
21. CAPITAL AND OPERATING COSTS	58
22. ECONOMIC ANALYSIS	59
23. ADJACENT PROPERTIES	59
24. OTHER RELEVANT DATA AND INFORMATION	59
25. INTERPRETATION AND CONCLUSIONS	59
25.1 Exploration.....	59
25.2 Resource Estimates	60
25.3 Mineral Reserve Estimates	60
26. RECOMMENDATIONS	60
26.1 Exploration Program.....	61
26.2 Geology, Block Modeling, Mineral Resources and Reserve	61
27. REFERENCES	64
CERTIFICATE	65
APPENDIX I	66
RESERVE BLOCKS BY MINE AREA	66

LIST OF TABLES

TABLE 1- 1	MINERAL RESOURCES INFERRED AND INDICATED, SAN MATÍN MINE.....	10
TABLE 1- 2	MINERAL RESERVE ESTIMATE PROVEN AND PROBABLE, SAN MARTIN MINE	11
TABLE 14- 1	INFERRED AND INDICATED MINERAL RESOURCES AT THE SAN MARTÍN MINE.....	36
TABLE 15- 1	RESOURCES TRANSFORMED INTO RESERVES FROM APR 2014 TO APR 2018	42

TABLE 15- 2 MINE PLANT RECONCILIATION SAN MARTIN MINE	43
TABLE 15- 3 PROVEN AND PROBABLE MINERAL RESERVES, EFFECTIVE DATE APRIL 30, 2018	44
TABLE 16- 1 SIM LIST OF MINE EQUIPMENT IN THE SAN MARTIN MINE PROJECT	52
TABLE 20- 1 LIST OF PERMITS OF THE SAN MARTIN MINE	56
TABLE 20- 2 NEIGHBORING COMMUNITY POPULATION AT SAN MARTIN MINE.....	58
TABLE 26- 1 DRIFTING AND DRILLING BUDGET FOR 2018	61

LIST OF FIGURES

FIGURE 4- 1 LOCATION MAP OF THE SAN MARTIN MINE PROJECT	17
FIGURE 4- 2 SAN MARTIN AND SURROUNDING AREA PROPERTY MAP.....	18
FIGURE 5- 1 PHYSIOGRAPHIC MAP OF MEXICO SHOWING THE LOCATION OF THE SAN MARTIN MINE.....	21
FIGURE 7- 1 GENERALIZED REGIONAL GEOLOGIC MAP OF THE SAN MARTÍN MINE PROJECT (AFTER LABARTHE, ET. AL, 2004)	25
FIGURE 7- 2 GENERALISED STRATIGRAPHIC COLUMN OF THE SAN MARTIN MINE REGION	26
FIGURE 9- 1 ON THE LEFT THAT GEOLOGIC MAP OF THE DISTRICT SHOWING THE SAN MARTIN STRUCTURE AND THE SANTA ELENA VEIN, TO THE NE AND SW. ON THE RIGHT, A MICROSTRUCTURE ON THE SOYATAL FORMATION THAT IS A MIRROR OF THE MAJOR STRUCTURE OF SAN MARTIN. SOURCE: CMPB GEOLOGY DEPARTMENT.....	29
FIGURE 13- 1 FLOWSHEET OF THE MILL PROCESS AT SAN MARTIN MINE PROJECT	34
FIGURE 15- 1 TYPICAL VERTICAL LONGITUDINAL SECTION (VLP) SHOWING THE BLOCKS OF PROVEN AND PROBABLE ORE IN THE SAN JOSÉ II OREBODY.	45
FIGURE 15- 2 GENERAL VERTICAL LONGITUDINAL SECTION OF THE SAN MARTIN MINE SHOWING THE PROVEN AND PROBABLE RESERVE BLOCKS.	46
FIGURE 18- 1 PORTAL OF THE INCLINE FOR THE SAN MARTIN MINE.....	53
FIGURE 18- 2 INSTALLATIONS OF MILL AT THE SAN MARIN MINE	54
FIGURE 18- 3 OFFICE BUILDINGS FOR THE MINE. OPERATION OF THE FURNACE AT THE SAN MARTIN ASSAY LABORATORY.....	54
FIGURE 20- 1 REFORESTATION ON THE NE SIDE OF THE TAILINGS DAM AT SAN MARTIN.....	57

ACRONYMS AND ABBREVIATIONS

Abbreviation Description Unit

Au	Gold
AuEq	Gold equivalent
Ag	Silver
CIM	Canadian Institute of Mining
cm	Centimetre
CMPB	Compañía Minera Peña de Bernal
CPG	Certified Professional Geologist
CRF	Cemented Rock Fill
COO	Chief Operating Officer
E	East
ep	epidote
Fe	iron
FA	Fire Assay
g	gram
g/t	grams per tonne
gpt	grams per tonne
ha	hectare
HQ	drill core size (63.5 mm)
ICP	Inductively Coupled Plasma
INEGI	Instituto Nacional de Estadística y Geografía
IP	induced polarization
K-spar	Potassium feldspar
kg	kilogram
km	kilometre
l	litre
LOM	Life of Mine
m	metre
m.a.s.l.	metres above sea level
mm	millimetre
m ²	square metre
m ³	cubic metre
M	million
Ma	Million years
MX\$	Mexican peso
N	North
NE	Northeast
NI 43-101	National Instrument 43-101 Standards of Disclosure for Mineral Projects
NQ	drill core size (47.6 mm)
NSR	Net Smelter Return
NW	Northwest
Ox	oxide
oz	troy ounce
oz/t	ounce per tonne
PENBER	Peña de Bernal Lab

P.Eng	Professional Engineer
P.Geo	Professional Geologist
ppb	parts per billion
ppm	parts per million
QA/QC	Quality Assurance/Quality Control
Qtz	Quartz
QP	Qualified Person
S.A. de C.V.	Sociedad Anónima de Capital Variable
SE	Southeast
SEMARNAT	Secretaría del Medio Ambiente y Recursos Naturales
Ser	sericite
SG	specific gravity
SRM	standard reference material
SIM	Starcore International Mines LTD
SW	Southwest
ton	tonne
US\$	United States dollar
UTM	Universal Transverse Mercator
W	West
WGM	Watts, Griffis & McQuat, Ltd
WGS	World Geodetic System
%	percent
°C	degree Celsius

Gold equivalent

$$AuEq \left(\frac{g}{t} \right) = Au \left(\frac{g}{t} \right) + \left(Ag \left(\frac{g}{t} \right) / 81 \right)$$

Contained ounces

$$oz Au = \left[\frac{Au \frac{g}{t} \times tonnes}{1000} \right] \times 32.1507$$

1. SUMMARY

1.1 Introduction

In June 2018, Erme Enriquez was retained by Salvador Garcia, Chief Operations Officer (COO) for Starcore International Mines LTD (“SIM”), to perform an Updated Reserve and Resource Estimate in the San Martin Mine, in accordance with the reporting requirements of Canadian National Instrument 43 101 (“NI 43 101”) and Form 43-101F1.

The Mineral Reserve update was performed by the San Martín’s mine personnel, all employees of SIM. SIM also provided the sections on geology, mining methods, project infrastructure, market studies and contracts, capital and operating costs, and economic analysis and a part of the conclusions and recommendations

Erme Enriquez is a Qualified Person under NI 43-101 and have no affiliation with SIM except that of independent consultant/client relationships. Mr. Enriquez has been an employee of Minas Luismin, first owner of San Martín, and then of Wheaton River, for more than 21 years and he participated in the supervision of the exploration and exploitation of San Martin from 1993 to 2003. Mr. Enriquez was responsible for assembling all items of the technical report and for preparing the Mineral Resource Estimate.

The effective date of this technical report is April 30, 2018.

1.2 Property Description and Location

The San Martin mine is located 47 kilometres, in straight line, northeast of the Queretaro City, Queretaro State, on local road No.100 and about 250 kilometres NW of Mexico City, near the towns of Tequisquiapan and Ezequiel Montes. The San Martin mine underground mine has been in operation since 1993.

The San Martin mine complex consists of 8 mining claims that cover 15,316 hectares. The total annual land-holding costs are estimated to be US\$105,190 dollars. All mineral titles and permits are held by Compañía Minera Peña de Bernal, S. A. de C. V. (CMPB), a direct, wholly-owned subsidiary of SIM. A 3.0% net smelter returns royalty (“NSR”) is payable to Servicio Geológico Mexicano (“SGM”- Mexican Geological Survey) on the claims San Martin Fracc. A, Title 215262, San Martin Fracc. B, Title 215263 and San Martin Fracc. C, Title 215264.

1.3 Exploration and Mining History

The deposit was discovered in the 18th century and high-grade mineralization reportedly was exploited by the Spaniards for approximately 40 years, however, no production records exist. The first records show the Ajuchitlán Mining and Milling Company produced an estimated 250,000 tonnes at a grade of 15 g Au/t and 100 g Ag/t from 1900 to 1924.

In 1982, the Mexican government, through the Council of Mineral Resources (CRM) put a mining claim of 6,300 hectares which covered the area of the mine in its central part. In 1986 Minas Luismin negotiated with the CRM an option in the mining claims of his property for a payment of US \$ 250,000 dollars and a royalty of 5%, which latter was reduced to 3% in 1996. Exploration begins with Luimin and at the end of 1993 the exploitation begins with an open pit in the San José oreshoot. This open-pit changes to underground when it is discovered that it was

not a disseminated Carlin-type deposit, but that it was a vein structure; then, in mid-1994, the underground works began in the same San José and San Martín oreshoot.

In the year 2000 the operation began mining some of the steeply dipping vein structures known as “tronco” and “manto” deposits. Over the last 17 years that mining has at times been predominantly from those oreshoots.

Over the period August 1, 2013 to April 30, 2018 the mine operated at an average 755 tpd using mechanized mining equipment such as single boom jumbos, 3.5-yard scooptrams and 10 to 20 tonne haulage trucks. In Conventional jackleg drills are still used in some of the mine headings.

1.4 Gold and Silver Processing and Recovering

The most relevant mineral processing and recovery information is derived from the results of the modern operations at the San Martín mine that began in 1993. Processing was done by crushing, grinding, and tank leaching with cyanide, followed by precipitation with zinc dust and in-house smelting of the precipitate to produce silver-gold doré. Records show that from 1993 through 2017, the mill processed over 6.3 million tonnes of ore with average head grades of 2.96 grams Au/tonne and 43 grams Ag/tonne. During this 17-year period, the mill recovered, on average, 82.2% of the contained gold and 55.5% of the contained silver.

1.5 Geology and Mineralization

The San Martín gold-silver district hosts classic, medium-grade gold-silver, epithermal vein deposits characterized by low sulphidation mineralization and adularia-sericite alteration. The San Martín veins are typical of most other epithermal silver-gold vein deposits in Mexico in that they are primarily hosted in the Upper Cretaceous black limestone and calcareous shales of the Soyatal-Mexcala Formation. Tertiary Lower Volcanic series of rhyolite flows, pyroclastics and epiclastics, overlain the sediments.

Mineralization at San Martín occurs in association with an epithermal low sulphidation, quartz-carbonate, fracture-filling vein hosted by a structure trending approximately N40°-60°E, dipping to the 50° to 90° to the southeast.

The Sn Martín structure has been known in different stages of exploration and has adopted several names, San José, San José II, San Martín, Cuerpo 28, Cuerpo 29, Cuerpo 30 and Cuerpo 31. The structure itself is offset by a series of faults of northeast trending that divides the oreshoots. The structure behaves vertical at the San José and San Martín areas (Tronco) and becomes flatter from Cuerpo 28 to 31 (Mantos).

The San Martín vein itself has been known underground traced for 2 km along trend, with widths between 1.5 to 10 metres and averages approximately 4.0 m. A secondary mineralized vein is located, both in the footwall and hangingwall, of the San Martín vein. This structure is the Santa Elena and represents an excellent target for exploration to the NE and SE of San Martín.

1.6 Mineral Resources Estimate

The mineral resource estimation for the San Martín Mine was completed in accordance to the guidelines of Canadian National Instrument 43-101 (“NI 43-101”). The modeling and estimation of the mineral resources were completed in April 30, 2018 under the supervision of Erme Enriquez, qualified person with respect to mineral resource estimations under NI 43-101.

The effective date of the resource estimate is April 30, 2018. Mr. Enriquez is independent of SIM by the definitions and criteria set forth in NI 43-101; there is no affiliation between Mr. Enriquez and SIM except that of independent consultant/client relationships.

The San Martin resources are classified in order of increasing geological and quantitative confidence in Proven and Probable, Inferred and Indicated categories in accordance with the “CIM Definition Standards – For Mineral Resources and Mineral Reserves” (2014) and therefore NI 43-101, as is the Inferred Resources category.

In the years prior to mining by CMPB reserve and resource estimates were based on the assumptions and subject to rules defined by Luismin many years ago. In recent years, with the involvement of various professionals, it was recognized that mining methodology was changing due to factors such as:

- a greater percentage of production coming from narrow to wide steeply dipping vein structures.
- Sub-horizontal Mantos mineralized structures that were somewhat narrower than historical Mantos.
- Reopening and scavenging of the footwall mineralization in old stopes where lower grade mineralization was not mined during times of lower gold prices.

Based on the above mining changes and incorporating mining experience over the last 7 years some of the original Luismin assumptions have been modified to improve tonnage and grade estimation for reserves. The assumptions used in this estimate are:

- A gold price of \$1300 per ounce.
- A silver price of \$16.00 per ounce.
- First quarter 2018 operating costs of US\$69.41 per metric dry tonne.
- Average metallurgical recoveries of 88% for gold and 55% for silver.
- Using the above price and cost assumptions the resultant calculated cutoff grade is approximately 1.66 g/t Au equivalent.
- Specific gravity of 2.6 g/cm³ has been applied to all calculated mineralized volumes.
- Mining dilution is applied to in situ mineralized zones, and recovery factors are applied to these diluted blocks using the following factors:
 - ✓ Mining dilution of 20% of zero grade in horizontal mineralized zones (Mantos) mined by room and pillar.
 - ✓ Mining dilution of 20% of zero grade in steeply dipping mineralized zones mined by cut and fill. This dilution factor is modified by first applying a minimum 2-meter mining width to narrow zones.
 - ✓ Remnant pillars left in room and pillar stopes are typically 20% of the total tonnage, i.e. 80% extraction. This recovery factor has been applied to subhorizontal mineralized zones.

In addition to these factors reserve grades are lowered to reflect mined grades in ore blocks that have sufficient historical production to establish that mined grades are lower than estimated from exploration data. The reserves and resources estimated in this report are based on data available up until April 30, 2018.

The mineral resources reported herein are classified as Measured, Indicated and Inferred according to CIM Definition Standards.

Total Inferred Mineral Resources at the San Martín mine, estimated by SIM, are **about 1,495,812 tonnes at a grade of 1.94 g Au/t and 25 g Ag/t**. Inferred and Indicated Mineral Resources are not known to the same degree of certainty as Mineral Reserves and do not have demonstrated economic viability. A summary of resources is in Table 1-1.

**Table 1- 1 Mineral Resources Inferred and Indicated, San Martín Mine
Compañía Minera Peña de Bernal, SA de CV
Mineral Resource Estimate
(as of April 30, 2018)**

Mine	Tonnes	Grade		Total Contained oz		
		(Au g/t)	(Ag g/t)	(oz Au)	(oz Ag)	(oz Au Eq)
San Jose II						
Inferred	178,871	1.73	10	9,935	57,578	9,579
San Martín						
Inferred	454,288	1.82	11	26,563	153,528	25,607
Inferred	410,400	1.76	16	23,289	206,350	23,245
Retaques SM						
Inferred	20,209	1.80	13	1,170	8,447	1,146
Cuerpo 28						
Inferred	182,684	2.44	88	20,666	513,925	26,991
4-700						
Inferred	92,918	1.77	36	5,295	108,115	5,963
Total Inferred	1,339,370	1.87	24	86,917	1,047,943	99,814
San Martín						
Indicated	156,442	2.56	27	12,883	136,711	13,109
Total Indicated	156,442	2.56	27	12,883	136,711	13,109
Total Inferred + Indicated	1,495,812	1.94	25	99,800	1,184,654	112,924

- Resources are valid as of April 30, 2018 as defined by end of month April 2018 topography.
- Measured, Indicated and Inferred resource cut-off grades were 1.66 g/t gold equivalent at San Martín.
- Mineral resources are not mineral reserves and do not have demonstrated economic viability. There is no certainty that all or any part of the mineral resources estimated will be converted into mineral reserves.
- Metallurgical recoveries were 88% gold and 55% silver.
- Gold equivalents are based on a 1:81 gold: silver ratio. $Au Eq = gAu/t + (gAg/t \div 81)$
- Price assumptions are \$1300 per ounce for gold and \$16.00 per ounce for silver for resource cutoff calculations.
- Mineral resources are estimated exclusive of and in addition to mineral reserves.
- Resources are constrained by a conceptual underground mining using parameters summarized in section.
- Resources were estimated by SIM and reviewed by Erme Enriquez CPG.
- Mineral Resources that are not Mineral Reserves do not have demonstrated economic viability.

1.7 Mineral Reserve Estimate

Total Proven and Probable Mineral Reserves at the San Martin mine as of April 30, 2018 estimated by SIM and reviewed by Erme Enriquez are **1,651,318 tonnes at a grade of 2.11 g Au/t and 33 g Ag/t** (Table 1-2).

Table 1- 2 Mineral Reserve Estimate Proven and Probable, San Martin Mine

Compañía Minera Peña de Bernal, SA de CV
Mineral Reserve San Martin Mine
(as of April 30, 2018)

Category	Tonnes	Grade		Total Contained oz		
		(g Au/t)	(g Ag/t)	(oz Au)	(oz Ag)	(oz Au Eq)
Proven	409,879	2.57	60	33,910	765,096	52,952
Probable	1,241,439	1.96	24	78,049	934,112	101,429
Total						
Proven and Probable	1,651,318	2.11	33	111,958	1,699,208	154,382

- Reserve cut-off grades are based on a 1.66 g/t gold equivalent.
- Metallurgical Recoveries were 88% gold and 55% silver.
- Mining Recoveries of 90% were applied.
- Minimum mining widths were 1.5 meters.
- Dilution factors is 20%. Dilution factors are calculated based on internal stope dilution calculations.
- Gold equivalents are based on a 1:81 gold:silver ratio. $Au Eq = gAu/t + (gAg/t \div 81)$
- Price assumptions are \$1300 per ounce for gold and \$16 per ounce for silver.
- Mineral resources are estimated exclusive of and in addition to mineral reserves.
- Resources were estimated by SIM and reviewed by Erme Enriquez CPG.

1.8 Mining Operations

Mine production operations are in two distinct underground zones and one under one small open pit operation. Current mining is from zones, which are contiguous to, or nearby, earlier mined out areas.

The two underground zones are known as San José II and San Martín, while the open pit is the near surface remnants is now a closed operation. Production operations have been underway at the San Martin mine since May 1994. On top of the big breccia-vein the structure becomes a manto-like. Here the Cuerpo 28 and Cuerpo 29 orebodies have been exploited partially since 1998. A set of faults crosscut the structure and thrown down the continuous oreshoot and split it into several segments where Cuerpo 30 and Cuerpo 31 have been found.

The orebody geometry and geotechnical attributes of the ore and host rocks, in both underground zones, resulted in the selection of mechanized, trackless, room and pillar stoping, with post waste rock backfill and a poor mix of waste and cement, as the most suitable mining method for ore extraction. Ore recovered from these operations is hauled to surface by truck to the mill infrastructure, where it is crushed and milled.

The operations that were visited, by Mr. Enriquez, were dry, well-ventilated, very tidy and appeared to be run in an orderly manner. The development headings are well supported with regular patterned roof bolting, through mesh and shotcrete, as a standard throughout the mine. Initial mining experience in the Cuerpo 28 zone indicated that dilution from waste wall rock and waste is greater than predicted in previous reports. SIM has introduced measures to reduce the dilution and also to increase ore recovery.

Dilution has been controlled with cemented waste rock as the fill medium. The experience with dilution from this waste rock backfill is not affecting the cost per ounce produced from treating lower grade ore, suggests that this backfill system, involving some combination of rock and cement, may have been more economic and safe.

In addition to overall cost reduction programs, including trials of bulk emulsion explosives, SIM management is implementing mine design modifications to reduce the ratio of waste development to ore tonnes and consequently the reduction in mining costs.

1.9 Conclusions and Recommendations

The QP considers the San Martín resource and reserve estimates presented here to conform with the requirements and guidelines set forth in Companion Policy 43-101CP and Form 43-101F1 (June 2011), and the mineral resources and reserves presented herein are classified according to Canadian Institute of Mining, Metallurgy and Petroleum (“CIM”) Definition Standards - For Mineral Resources and Mineral Reserves, prepared by the CIM Standing Committee on Reserve Definitions and adopted by CIM Council on May 10, 2014. These resources and reserves form the basis for SIM’s ongoing mining operations at the San Martín Mines Project.

The QP is unaware of any significant technical, legal, environmental or political considerations which would have an adverse effect on the extraction and processing of the resources and reserves located at the San Martín Mines Project. Mineral resources which have not been converted to mineral reserves, and do not demonstrate economic viability shall remain mineral resources. There is no certainty that all or any part of the mineral resources estimated will be converted into mineral reserves.

The QP considers that the mineral concessions in the San Martín mining district controlled by SIM continue to be highly prospective both along strike of the structure and down dip of the existing mineralization and adjacent structures that have high geological potential.

SIM’s San Martín Mines Project has an extensive mining history with well-known gold and silver bearing vein systems. Ongoing exploration has continued to demonstrate the potential for the discovery of additional resources at the project and within the district surrounding the mine.

Since SIM took control of the San Martín Mines Property, new mining areas have enabled to continue production by providing additional sources of mill feed. SIM’s operation management teams continue to search for improvements in efficiency, lowering costs and researching and applying low-cost mining techniques.

Although the reconciliations conducted by SIM show good comparisons on planned values versus actual values the reconciliation process should be improved to include the estimated tonnes and grade from the resource models. By comparing the LOM plan monthly to the plant production, the actual physical location of the material mined may be different in the plan versus

the actual area that was mined. Due to the many faces that are mined during a day this can only be completed on an average monthly basis to account for the blending of this material at the mill. The monthly surveyed as mined areas should be created and saved monthly for reporting the modeled tonnes for each month. The model predicted results versus actuals can then be used to determine if dilution factors need to be adjusted or perhaps the resource modeling parameters may require adjustment if there are large variances. On a yearly basis, the mill production should be reconciled to the final doré shipments and resulting adjustment factors should be explained and reported.

2. INTRODUCTION

2.1 Issuer and Terms of Reference

Starcore International Mines LTD (“SIM”) is a Canadian based mining and exploration company actively engaged in the exploration, development, and production of mineral properties in Mexico. SIM is headquartered in Vancouver, British Columbia with management offices in Mexico City, Mexico, and is listed on the Toronto (TSX:SAM) and Frankfurt (FK:V4JA) stock exchanges. The company has one currently active mining property in Mexico, the San Martín Property in northeast Queretaro State. SIM has retained Mr. Enriquez to complete an independent technical audit and update of the mineral resource and reserve estimates for the San Marín Mine Project (the “Project”) located within the Municipality of Colón. This report presents the results of Mr. Enriquez efforts, and is intended to fulfill the Standards of Disclosure for Mineral Projects according to Canadian National Instrument 43-101 (“NI 43-101”).

This report was prepared in accordance with the requirements and guidelines set forth in NI 43-101 Companion Policy 43-101CP and Form 43-101F1 (June 2011), and the mineral resources and reserves presented herein are classified according to Canadian Institute of Mining, Metallurgy and Petroleum (“CIM”) Definition Standards - For Mineral Resources and Mineral Reserves, prepared by the CIM Standing Committee on Reserve Definitions and adopted by CIM Council on May 10, 2014. The mineral resource and mineral reserve estimates reported here are based on all available technical data and information as of April 30, 2018.

2.2 Source of Information

A portion of the information and technical data for this study was obtained from the following previously filed NI 43-101 Technical Reports:

Spring, V., McFarlane, G.R., 2002, A Technical Review of the Tayoltita, Santa Rita, San Antonio, La Guitarra and San Martin Operating Silver and Gold Mines in Mexico. Watts, Griffis and McOuat NI 43-101 report prepared for Wheaton River Minerals Ltd.

Spring, V. (2005), An Audit of the Mineral Reserves/Resources Tayoltita, Santa Rita, San Antonio, and San Martin Mines as of December 31, 2004. For Wheaton River Minerals LTD.

Gunning, D. R. and Whiting, B., 2009, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2009. For Starcore International Mines LTD.

Gunning, D. R. and Campbell, J., 2011, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2011. For Starcore International Mines LTD.

Campbell, J., 2012, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2012. For Starcore International Mines LTD.

Gunning, D. R., 2013, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2013. For Starcore International Mines LTD.

Gunning, D. R. and Campbell, J., 2014, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2014. For Starcore International Mines LTD.

2.3 Qualified Person

Mr. Enriquez, E., CPG, has over 30 years of professional experience as geologist, both as an employee and a consulting geologist and has contributed to numerous mineral resource projects, including silver, gold and polymetallic resources throughout Mexico past fifteen years. Mr. Enriquez is responsible for the full content of this report.

As Qualified Person Mr. Enriquez conducted an on-site inspection of the San Martín property during June 12 to 15, 2018. While on site, Mr. Enriquez reviewed SIM's current operating procedures and associated drilling, logging, sampling, quality assurance and quality control (QA/QC), grade control, and mine planning (short, medium, and long term) procedures, also inspected the laboratories at the San Martín facilities as well as the underground operations and plant.

Mr. Enriquez met with the general mine manager and all personnel of the geology department to review the geologic understanding, sampling methods and types, modeling (resources, reserves, and grade control), prior to inspecting the procedures in the mine and office for collecting and handling the data. Once the geology department processes were reviewed, Mr. Enriquez discussed with the mine planning and survey department the process for short, medium, and long-term mine planning. Reconciliation was discussed with both departments and the plant supervisors. The assay laboratory was toured, and the procedures were reviewed with the laboratory superintendent.

2.4 Units and Currency

All units used in this report are in a metric system. Tonnages are shown as tonnes (1,000 kg), linear measurements as metres ("m"), or kilometres ("km") and precious metal values as grams ("g"). Grades are grams of gold per tonne ("Au g/t"), and grams of silver per tonne ("Ag g/t"). All economic data is quoted in US dollars ("US\$"). When peso amounts required conversion into US dollars, the peso exchange rate used was 18.5 pesos equivalent to US\$1.00 as this was the rate used in the 2018 mine operating budget.

3. RELIANCE ON OTHER EXPERTS

The author of this report is Qualified Person for those areas as identified in the Certificates of Qualified Person attached to this report. In preparing this report, the author relied heavily on various geological maps, reports and other technical information, mostly unpublished proprietary information collected on-site and provided to the author by SIM.

Much of the original information is in Spanish and English, with translations from Spanish to English of key and relevant technical documents provided by SIM. For this current report, most of the technical information was translated by geologist employed by SIM, although legends and annotations on many of the maps and sections are in Spanish or have been translated to English. I occasionally checked a few key parts of the translations and found them good.

From my experience on this report and the other previous reports I have done for other companies, I believe the translations provided to us are credible and generally reliable, but I cannot attest to their absolute accuracy.

Overall, the technical information I reviewed is very well-documented, comprehensive and of good technical quality. It clearly was gathered, prepared and compiled by various competent technical persons, but not necessarily Qualified Persons as currently defined by NI 43-101. In recent years, the voluminous information collected by SIM has been carefully reviewed by Mr. David R. Gunning, P. Eng. And Joseph W. Campbell, P. Geo. whom are a Qualified Persons as defined by NI 43-101.

Because I am not expert in land, legal, environmental and related matters, I have relied (and believe there is a reasonable basis for this reliance) on various other individuals who contributed the information regarding legal, land tenure, corporate structure, permitting, land tenure and environmental issues discussed in this report. Specifically, David Gunning and Joseph Campbell, both experienced independent Qualified Person as defined by NI 43-101.

This report summarizes the Mineral Resource/Reserve estimates for the San Martin Project, effective as of April 30, 2018 using the procedures which have been audited by both PAH and WGM in the past. These procedures have been verified by David R. Gunning, P. Eng. And Joseph W. Campbell, P. Geo, whom virtue of their education and experience is an independent Qualified Persons as defined by NI 43-101.

4. PROPERTY DESCRIPTION AND LOCATION

4.1 Location

The San Martin Mine is located 47 km in a straight line to the NE of the city of Queretaro, 10 km NW of Ezequiel Montes, 4 km SW of the Peña de Bernal and 25 km to the NW of Tequisquiapan, in the State of Querétaro. Territorially, it is located within the municipality of Colón, at the UTM coordinates of 398,300E and 2292,530N and an average elevation of 2,130 m.a.s.l. (Figure 4-1)



Figure 4- 1 Location map of the San Martin Mine Project

4.2 Property Description

Compañía Minera Peña de Bernal S.A. de C.V., a wholly owned SIM subsidiary, holds eight mining concessions covering 15,317 ha at the San Martin Mine in the State of Querétaro (Figure 4-2) Right payments are done twice a year, every semester. The San Martin Project presently

consists of two underground mines, San José and San Martín. The San Martín mine is approximately 800 m NNE of the San José mine. Minas Luismin, SA de CV commenced mining late in 1993 on the San José deposit with an open pit operation that was later abandoned and mining continued underground methods over the San José and the San Martín oreshoots. Mining regulations in Mexico provides that all concessions are to be valid for a period of 50 years. Taxes are based on the surface area of each concession and the time of expedition of the title and are due in January and June of each year. All tax payments have been paid by SMI to date. Currently, annual claim-maintenance fees are the only federal payments related to mining claims, and these fees have been paid in full to June 30, 2018. The current annual holding costs for the San Martín mining claims are estimated at US\$105,000 Dollars (Table 4-1).

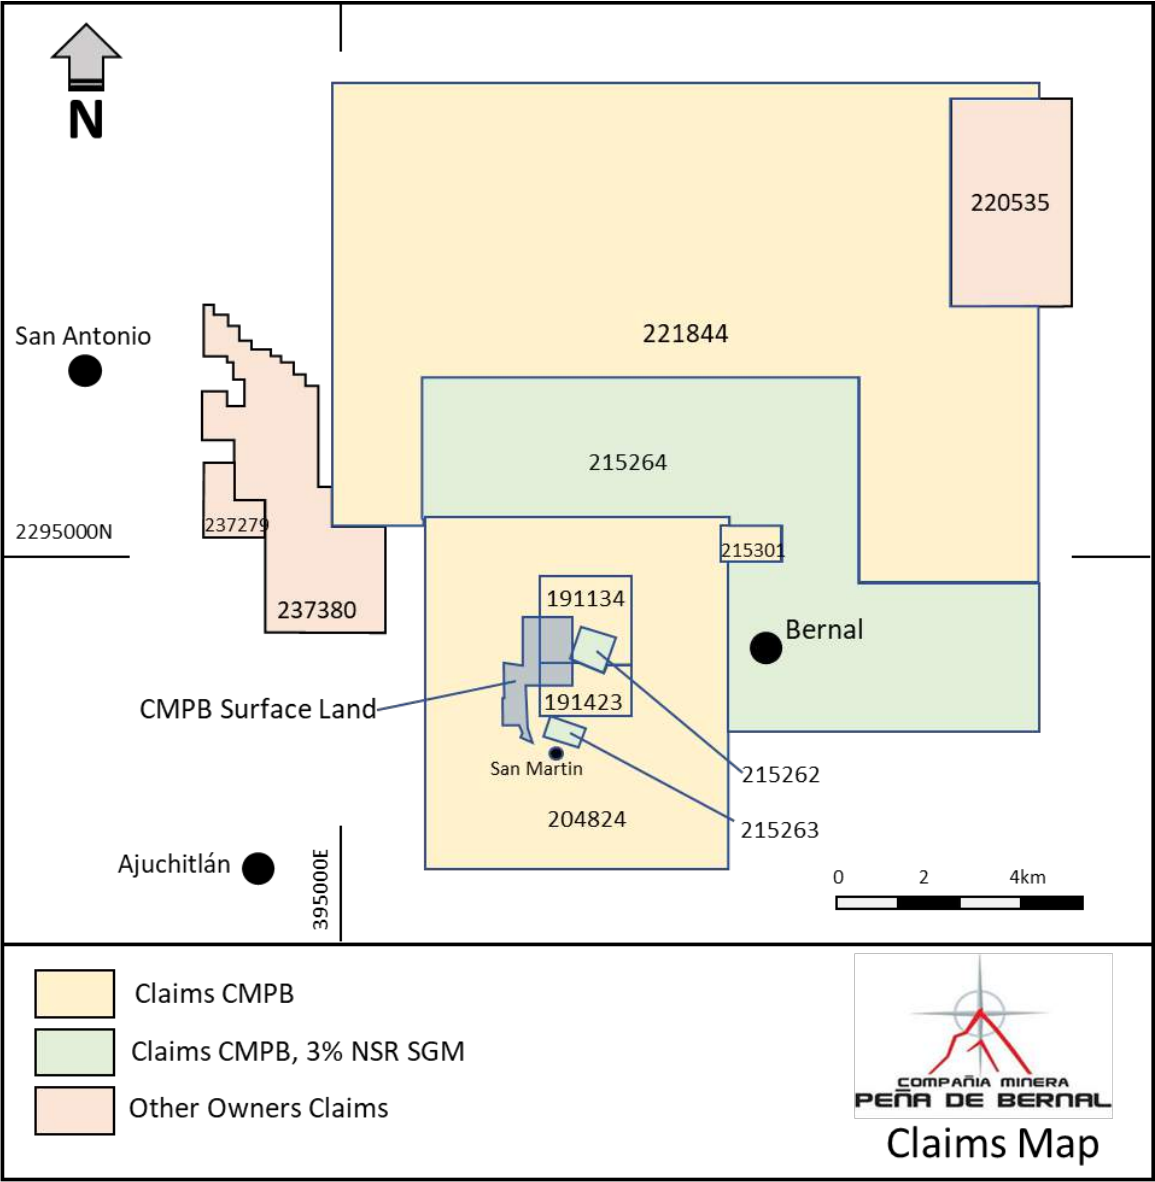


Figure 4-2 San Martín and Surrounding Area Property Map

Table 4- 1 List of Mining Titles for the San Martin Mine Project

Starcore International Mines LTD
Compañía Minera Peña de Bernal, SA de CV
Mining Concessions San Martin Mine

No. on Map	Concession Name	Exp.	Title	Term of Cession		Hectares	2018 Annual Taxes (Pesos)	
				From	To		1st Sem	2nd Sem
1	San Martin 2	321.1/6-72	191134	29/04/1991	28/04/2041	190.7972	\$ 30,157	\$ 30,157
2	San Martin	321.1/6-71	191423	19/12/1991	18/12/2041	132.0818	\$ 20,856	\$ 20,856
3	La Trinidad	6/1.3/276	204824	13/05/1997	12/05/2047	2,610.7224	\$ 412,193	\$ 412,193
4	San Martin Fracc. A.	6/1.3/00409	215262	14/02/2002	13/02/2052	37.1099	\$ 5,861	\$ 5,861
5	San Martin Fracc. B.	6/1.3/00411	215263	14/02/2002	13/02/2052	22.8901	\$ 3,616	\$ 3,616
6	San Martin Fracc. C	6/1.3/00412	215264	14/02/2002	13/02/2052	3,182.5646	\$ 502,470	\$ 502,470
7	San Martin 3	6/1.3/00410	215301	14/02/2002	13/02/2052	60.0000	\$ 9,473	\$ 9,473
8	San Martín Cuatro	065/15357	221844	02/04/2004	01/04/2054	6,755.6145	\$ 1,066,606	\$ 1,066,606
Total						15,316.7805	\$ 2,051,232	\$ 2,051,232

4.3 Mineral Tenure, Agreements and Encumbrances

SMI acquired the San Martin Mine ("San Martin") from Goldcorp Inc. ("Goldcorp") in February 2007. Goldcorp is a Canadian mining company listed on both Canadian and United States Stock Exchanges. Goldcorp acquired the San Martin Project in February 2005 with the take-over of Wheaton River Minerals Ltd., who had acquired San Martin in the take-over in 2002 of the Mexican mining company Minas Luismin S.A. de C.V. ("Luismin"). SMI paid US\$24 million in cash and issued 4,729,000 common shares to Luismin at a deemed value of CDN\$0.50 per share in consideration for the shares of Bernal.

San Martin is owned and operated by Compañía Minera Peña de Bernal, S.A. de C.V., a wholly owned subsidiary of SMI.

SMI agreed to sell all silver produced from San Martin to Goldcorp Trading (Barbados), Inc., a subsidiary of Goldcorp, Inc., until October 2029, at the prevailing spot market rate at the time of sale of silver. The sale of silver is secured by a security interest over the San Martin Mine, which is subordinated to the interests granted to Investec.

5. ACCESSIBILITY, CLIMATE, LOCAL RESOURCES, INFRASTRUCTURE AND PHYSIOGRAPHY**5.1 Access**

The roads through which the San Martín mine is accessed are paved and they are in good condition all year long. It can be reached by highway No. 57 between the cities of Querétaro and San Luis Potosí. Access to the San Martin mine can be carried out also from Mexico City through highway 57D, for 160 kilometers, until reaching the city of Sn Juan del Río, Queretaro. From here, take the HW 120, for 19 km until Tequisquiapan, and continue for 16 km more until Ezequiel Montes. From here take the road to the junction with the # 100 highway, take this to the NE and 1.5 km more to enter the mine facilities.

From the City of Querétaro take Highway 45D for approximately 22 km to the SE and then take Highway # 100 to the NW for 36 kilometers until reaching the junction with the entrance to the

mine in the town of San Martin. This same road leads to the magical town of Peña de Bernal, which is the company's employee camp.

There are constant flights from the City of Querétaro to several destinations in the United States, particularly Los Angeles, Chicago, New York and Houston; although these change from season to season.

5.2 Climate

The climate in the mine area is semi-dry, described by generally low rates of precipitation. During the year, the temperature generally varies from 5 ° C to 30 ° C and rarely drops below 2 °C or rises above 33 °C.

The warm season lasts for two to three months, from April to June, and the average daily maximum temperature is over 28 °C. The hottest month is May. The cool season lasts around three months, from December to February, and the average daily maximum temperature is less than 24 °C. The coldest days of the year is January, with an average minimum temperature of 5 °C and an average maximum of 23 °C. The normal yearly temperature is 19°C.

The rainy season lasts six months, from June to November, with an average total accumulation of 509 millimeters. The dry season lasts from December to May.

5.3 Local Resources and Infrastructure

The city of Querétaro is the closest major population center to the San Martín Mine Project, with a population of approximately 802,000. Querétaro is an agricultural, commercial, tourist and mining center with all of the associated municipal amenities, including an international airport with numerous regional flights to other major Mexican cities and the United States.

At each of the mine sites, the water required is supplied from the dewatering of the mines. Industrial water for the cyanide plant is recycled, and additional water (60,000 m³/y of fresh water) is obtained from a nearby wells.

Electrical power from the Federal Electricity Commission (34 kV) supplies both the plant and mine, and satisfies power demand, which averages about 1.1 megawatts. Two emergency generators, one of 500 kW and other of 200 kW, provide power to the mill in case of outages.

An upgrade to the tailings dam was completed in 2010, when dry stacking of the tailings began, and current capacity is sufficient for many years of production. Apart from offices, dining room, warehouses, shop and other facilities, SMI also provides dormitories and limited housing facilities for employees working on a rotational schedule at the township of Ezequiel Montes and Bernal. Much of the labor work force lives in the San Martin town and nearby communities. The area has a rich tradition of mining and there is an ample supply of skilled personnel sufficient to man both the underground mining operations and the surface facilities.

SIM has negotiated access and the right to use surface lands sufficient for many years of operation. Sufficient area exists at the property for all needed surface infrastructure related to the life-of-mine plan, including processing, maintenance, fuel storage, explosives storage and administrative offices. There exists sufficient capacity in existing tailing impoundments for tailings disposal.

5.4 Physiography

The relief and landforms of Mexico have been greatly influenced by the interaction of tectonic plates. The resulting relief patterns are so complex that it is often claimed that early explorers, when asked to describe what the new-found lands were like, simply crumpled up a piece of parchment by way of response.

Figure (5-1) shows Mexico's main physiographic regions. The core of Mexico (both centrally located, and where most of the population lives) is the Volcanic Axis (Region 10 on the map), a high plateau rimmed by mountain ranges to the west, south and east. Coastal plains lie between the mountains and the sea. The long Baja California Peninsula parallels the west coast. The low Isthmus of Tehuantepec separates the Chiapas Highlands and the low Yucatán Peninsula from the rest of Mexico.

The San Martin Mine falls in the convergence of the Central Plateau, Sierra Madre Oriental and Volcanic Axis or Trans-Mexican Volcanic belt.

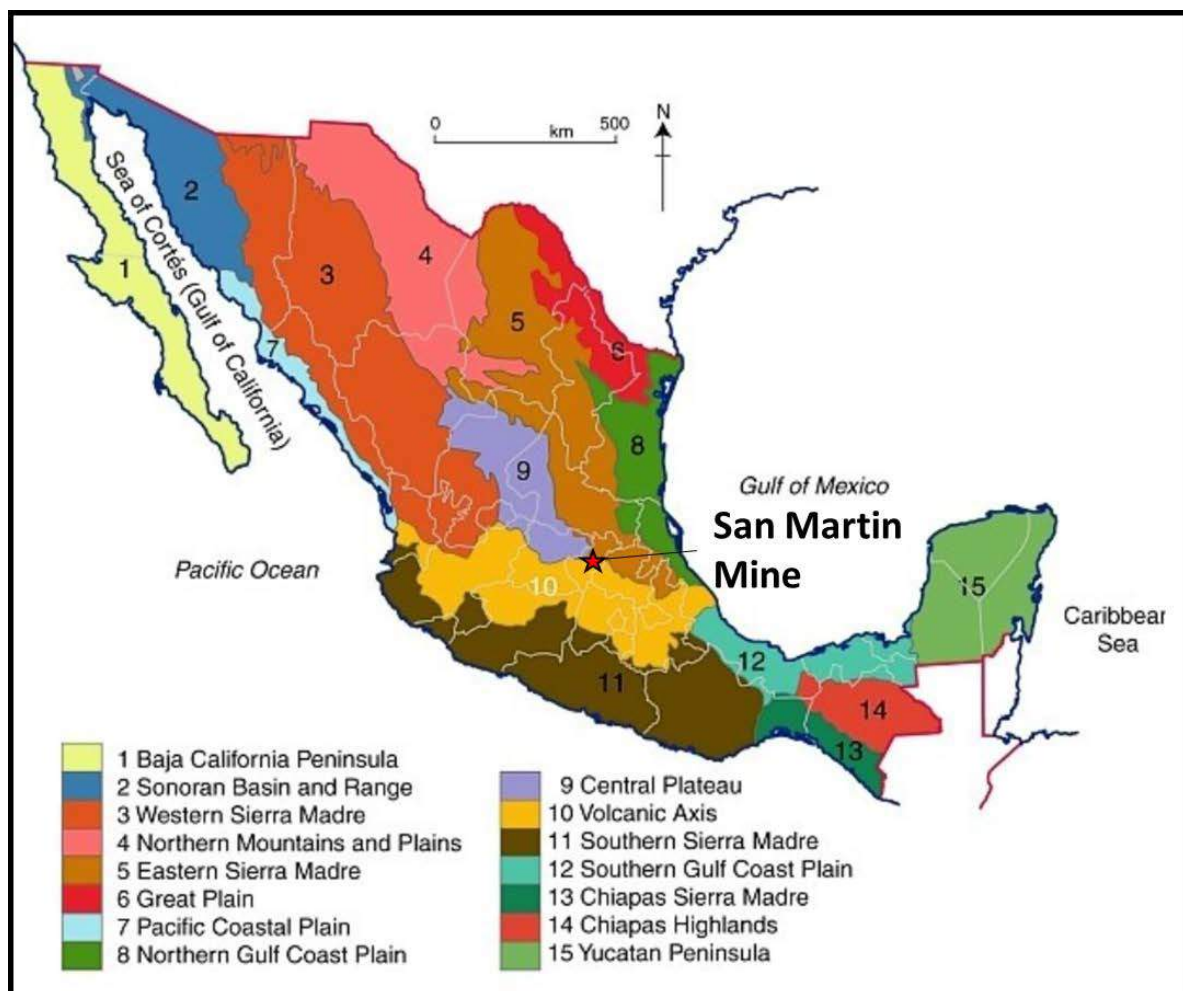


Figure 5- 1 Physiographic map of Mexico showing the location of the San Martin Mine

6. HISTORY

Mining in the San Martín district extends back to at least 1770 when the mines were first worked by the Spanish, particularly by Don Pedro Romero de Terreros, Count of Regla. Spaniards worked in the district for 40 years, however, there is no production records available for that time. During those days, silver and gold production accounted for 80% of all exports from Nueva España (New Spain), although, by the late-eighteenth century silver production collapsed when mercury, necessary to the refining process, was diverted to the silver mines of Potosí in present day Bolivia.

The vast majority of production came prior to the 1910 Mexican Revolution with San Martín district being an important producer. The first records show the Ajuchitlán Mining and Milling Company produced an estimated 250,000 tonnes at a grade of 15 g Au/t and 100 g Ag/t during 1900 to 1924.

The first modern stake was with 1982, when the Mexican government declared a 6,300 ha National Reserve over the area surrounding the Peña de Bernal. Luismin entered into an agreement to explore in the claims of CRM in 1986 for a payment of US \$ 250,000 dollars and a royalty of 5%, which latter was reduced to 3% in 1996. In 1988 geological reconnaissance and exploration program initiated. Geological works concluded in 1992 and by the end of 1993 the decision was made to start the open-pit mining in the San José area, at a rate of 300 tpd.

The operation of the San José pit only lasted a couple of years, when it was discovered that the deposit was not a "Carlin type", as had been thought, but that it was a tabular structure in vein that continued to deepen and laterally along its strike. Then it was decided to start the underground mining, on the same San José structure and on the oreshoot of San Martín, which ultimately turned out to be the one with the largest number of reserve and resources.

In the year 2000, the exploitation begins in the San Martín body, called "Tronco" due to its verticality. In 2001, at the same time, the exploration of high-grade gold bodies called "Mantos" began. The first of these oreshoots was the Body 28.

The mine is currently mined 850 tpd and the capacity of the mill is 1100 tpd. The mining method is cut and filled with dry backfill. The exploitation in the Body 28 is currently room and pillars filled with a mixture of backfill and 5% cement.

Historical production at the San Martín Mines Project for the years 1993 to April 30 2018 is roughly estimated in Table 6-1.

Table 6- 1 Summary of production for the San Martín Mine project (1993 to April 30, 2018)

Starcore International Mines LTD
Compañía Minera Peña de Bernal, SA de CV
San Martín Mine Project
Historical Production 1993-April 30 2018

Year	Tonnes	Grade		Production		
		Au (g/t)	Ag (g/t)	Oz Au	Oz Ag	Oz Au Eq.
1993	28,267	2.53	60	1,387	24,463	1,707
1994	134,118	3.19	35	13,179	81,605	14,298
1995	146,774	3.40	38	16,172	180,459	17,068
1996	187,691	3.40	44	19,553	155,160	21,620
1997	219,827	3.27	43	22,016	174,013	24,570
1998	224,279	3.45	50	23,680	210,680	27,539
1999	242,295	3.46	46	25,852	194,110	29,624
2000	284,490	3.61	54	31,209	245,310	35,571
2001	287,520	3.76	65	32,773	330,217	38,068
2002	268,451	4.26	71	35,634	370,406	41,124
2003	276,481	4.29	82	36,438	464,947	42,692
2004	272,734	4.47	83	36,935	458,681	44,377
2005	282,392	3.92	65	32,814	349,071	38,543
2006	278,914	2.82	52	22,004	235,806	26,529
2007	252,400	3.34	49	25,232	224,714	29,606
2008	266,600	2.50	33	18,733	159,877	21,367
2009	272,856	2.43	33	19,171	167,827	21,696
2010	275,290	2.03	30	15,492	163,489	18,156
2011	296,845	2.14	39	17,694	267,237	23,736
2012	309,796	2.09	25	16,197	160,678	19,213
2013	306,941	2.66	24	22,247	129,861	24,425
2014	311,210	2.35	22	20,062	112,010	21,755
2015	309,565	2.09	20	17,903	104,767	19,319
2016	286,278	1.94	16	14,606	68,463	15,547
2017	259,709	1.69	13	11,563	54,287	12,246
April 30 2018	99,067	1.59	36	4,410.96	64,459.38	5,218.98
TOTALS	6,380,790	2.96	43	552,957	5,152,597	635,614

7. GEOLOGICAL SETTING AND MINERALIZATION

7.1 Geology

The regional and local geology of the San Martín Mine Project is described in detail in several existing internal and previously published technical reports and other internal reports for SIM. The following descriptions of geology and mineralization are excerpted and/or modified from Labarthe, et. al (2006) and Rankin (2008). Mr. Enriquez has reviewed the available geologic data and information, and finds the information presented here in reasonably accurate and suitable for use in this report.

The San Martin area comprises Mesozoic shallow-basin sediments (shales and limestones) unconformably overlain by Tertiary volcanics/epiclastic and volcanoclastic sediments. Localized subvolcanic micro-granodiorite also occurs (Figure 7-1)

The primary formations are (from oldest to youngest): Jurassic: Las Trancas Formation(Jtr). This comprises massive to well bedded and laminar limestones. Very thin (<10cm) shale intercalations occasionally occur. A dark carbonaceous limestone is known from the deeper SE sections of the San Martin mine.

Cretaceous: El Doctor and Soyatal Formations. These comprise a lower pale buff to orange lithic shale, overlain by intercalated shale and limestone. Note that there may be some local problems in discrimination between the Cretaceous and Jurassic limestones in some outcrops and drill core; a zone of shallow-dipping limestones in the mine infrastructure area are shown in the geology map as Cretaceous Soyatal Formation.


Tertiary: Continental sediments, overlain by bimodal epiclastic, rhyolitic ignimbrite & andesite with a distribution around the mine site. The andesite has been dated at ~30 Ma. The volcanic breccias, lahar, epiclastic, ignimbrite and andesite are younger and have been dated at ~10–11Ma. The most conspicuous feature is the Peña de Bernal intrusive, which is a micro-granodiorite of an age of 35 Ma. See also Figure 7-2.

7.2 Mineralisation

Mineralisation occurs in Upper Cretaceous black limestone and calcareous shales of the Soyatal-Mezcala Formation as electrum, and silver selenide minerals principally associated with quartz and to a lesser degree with calcite. The deposit is an epithermal, low sulphidation precious metal (Au-Ag) type (metal ratio Ag: Au at 10:1).

Mineralisation is generally made up of breccia that commonly is concordant with a limestone/shale contact (in the San Martin and San José areas) which forms the relatively steeply dipping “Tronco” and “Mantos” oreshoots, these veins contact the younger volcanic flows (dacite and ignimbrite) where they have formed the more horizontal portions of the deposit. The mineralized economic breccia grades from 30 g Ag/t to 250 g Ag/t. Exploration has been concentrated along the NE trending breccia zone however evidence of a northerly trend in area 30 and 31 leads to suspect possible other structures together with 2.0 g Au/t to 30 g Au/t over widths that vary from 1.5 to 17.0 m but average 4.0 m.


The mineralised oreshoots show several stages of brecciation and cementation, with four major stages of hydrothermal breccias and supergene alteration that filled fractures and late cavities. The metallic mineralization is mainly formed by electrum, naumannite, tetrahedrite, pyrite and chalcopyrite as hypogene minerals, and free gold, partzite, chlorargyrite, malachite, hematite, goethite-limonite as supergene minerals. Gangue minerals are mainly quartz, chalcedony and calcite, with minor amounts of adularia. Quartz and calcite occur in all the four stages cementing the breccia fragments of rock and older vein. Chalcedony, quartz and calcite associated with the economic mineralization usually show saccharoid, crustiform, coliform, cockade and comb textures. Stage one is totally barren of silver and gold. The main Ag-Au mineralization occurred in the second stage of brecciation, associated to coliform and chalcedony quartz. Stage three is carrying low grade and is abundant. The late stage of mineralization is characterized by native gold content, chlorargyrite and abundant partzite, as a result of the supergene alteration. Mineralization occurs as native gold, electrum, naumannite (AgSe) and argentojarosite ($\text{AgFe}_3(\text{SO}_4)_2(\text{OH})_6$) associated principally with quartz and lesser calcite. The silver contained in argentojarosite is not recoverable with cyanidation.

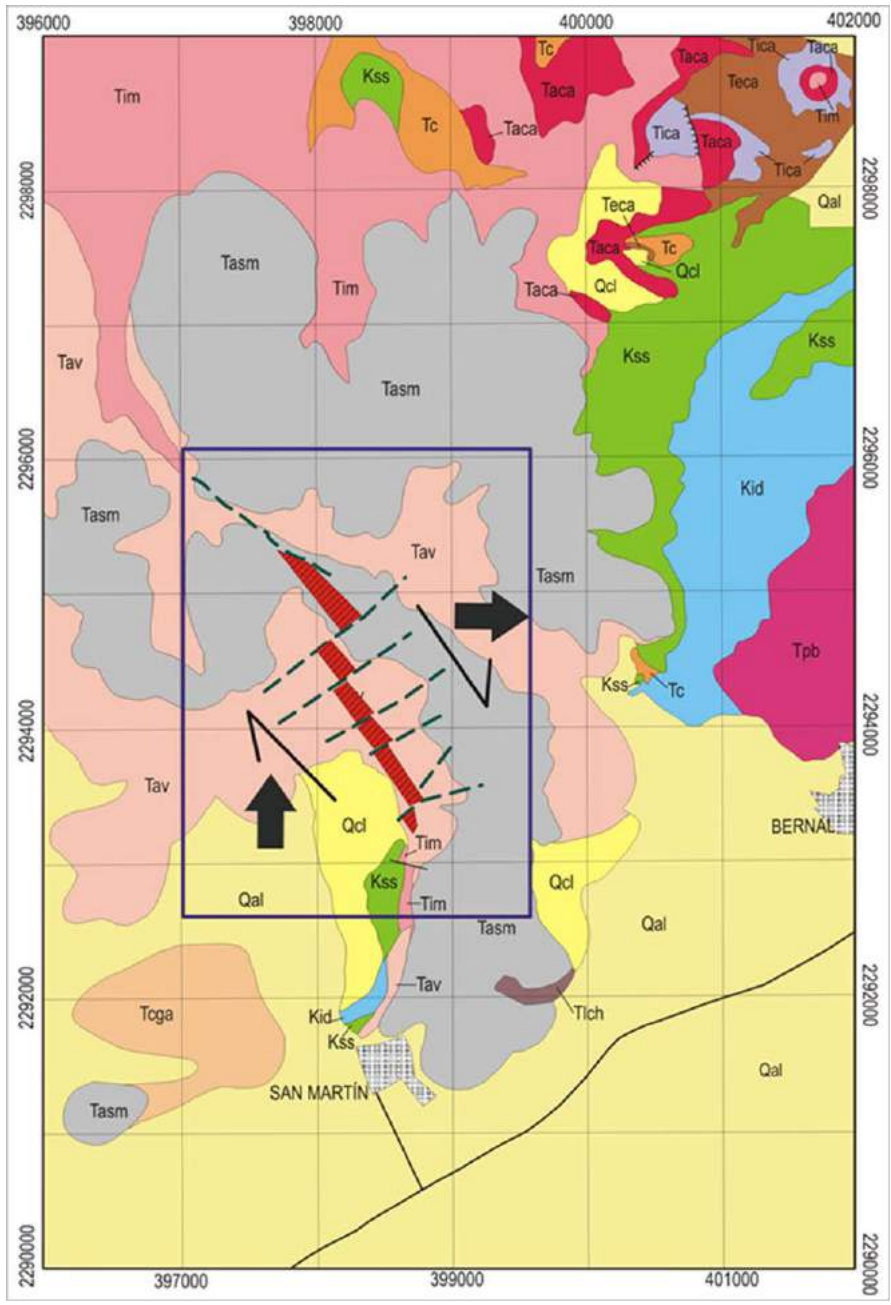

Figure

7-1

Generalized regional geologic map of the San Martín Mine Project (After Labarthe, et. al, 2004)

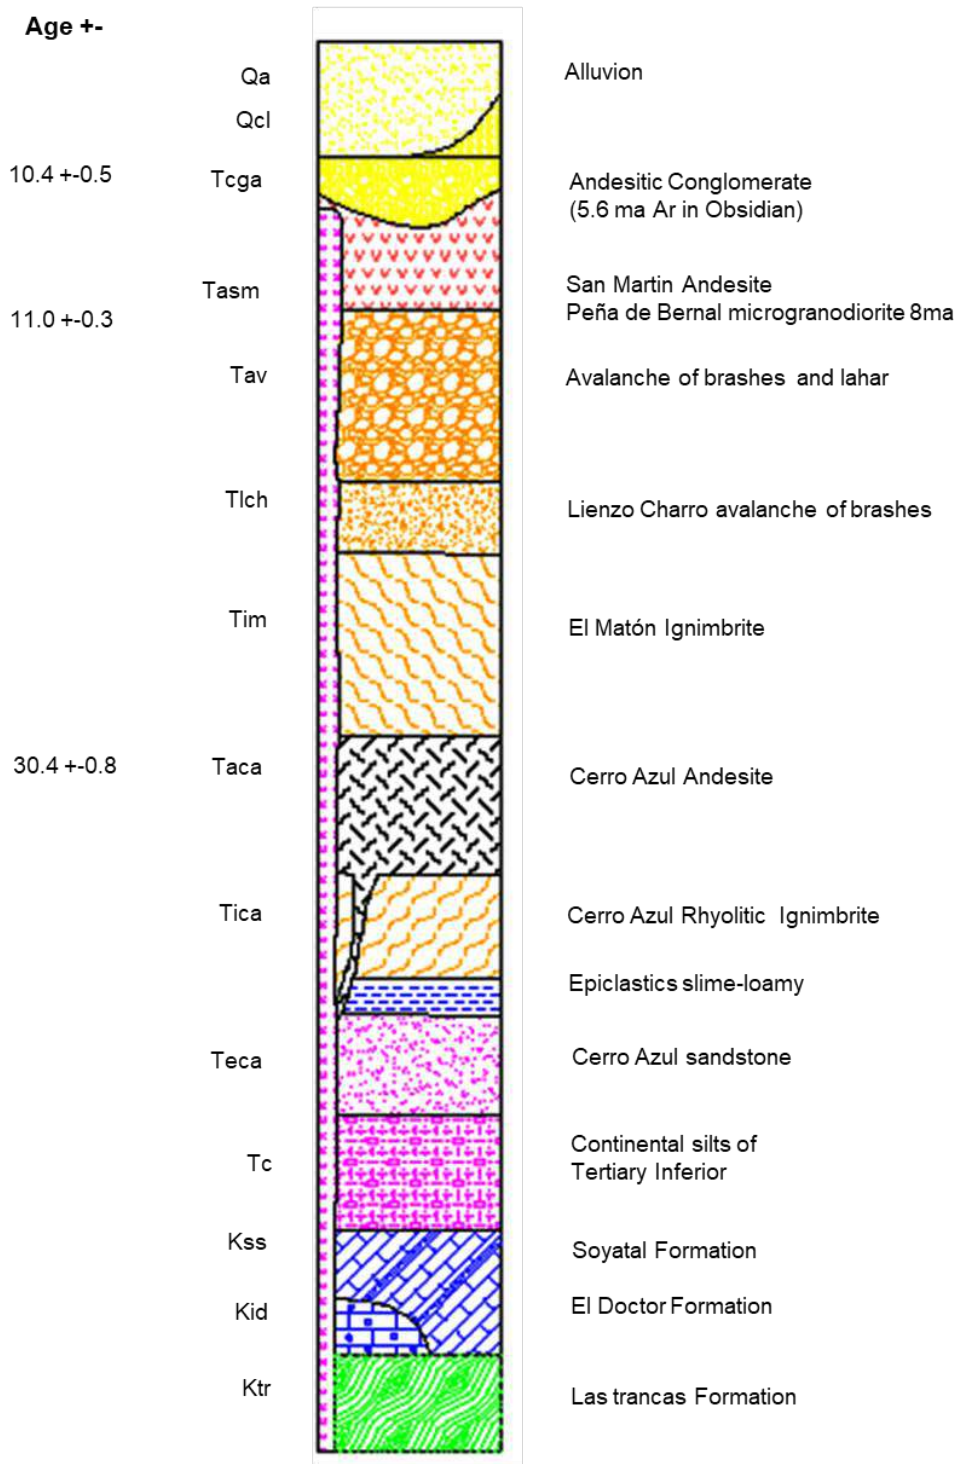

(Geology Department & Geology Institute U.A.S.L.P.)

Figure 7- 2 Generalised stratigraphic column of the San Martin Mine region

8. DEPOSIT TYPE

The San Martin deposit is composed by a tabular, vein-like subvertical mineralized structure that becomes to a sub-horizontal mineralized structure or “manto-like” close to surface. This mineralized structure is recognized for over 2 km along strike, with thicknesses between 1.5 and 17 metres and 400 m of vertical extent or “favourable zone”. In general, the mineralization is hosted in the contact of limestone-shale of Soyatal-Mexcala Formation and associated to a silicified rhyolitic dike.

Homogenization temperatures (Th) indicate that mineralization of the second stage occurred between 220 °C and 260 °C, with an average Th of 243 °C. Salinities range from 0.5 to 2.5 wt. % NaCl equiv., with an average of 1.9 wt. % NaCl equiv.

Low sulphidation epithermal veins in Mexico typically have a well-defined, sub-horizontal ore horizon about 300 m to 500 m in vertical extent where the bonanza grade ore shoots have been deposited due to boiling of the hydrothermal fluids (Buchanan (1981), Enriquez (1995)). Neither the top nor the bottom of the San Martin ore horizon has yet been found but, given that high gold-grade mineralization occurs over a 400-m vertical extent from the top of the San Martin oreshoot, to below Level 10 in the general mine, it is likely that erosion has not removed a significant extent of the ore horizon due to a capping of rhyolites on top of the structure.

Low sulphidation deposits are formed by the circulation of hydrothermal solutions that are near neutral in pH, resulting in very little acidic alteration with the host rock units. The characteristic alteration assemblages include illite, sericite and adularia that are typically hosted by either the veins themselves or in the vein wall rocks. The hydrothermal fluid can travel either along discrete fractures where it may create vein deposits, or it can travel through permeable lithology such as a volcanic rocks, limestone or shale, where it may deposit its load of precious metals in a vein deposit. In general terms, this style of mineralization is found within the San Martin district.

Figure 8-1 illustrates the spatial distribution of the alteration and veining found in a hypothetical low sulphidation hydrothermal system.

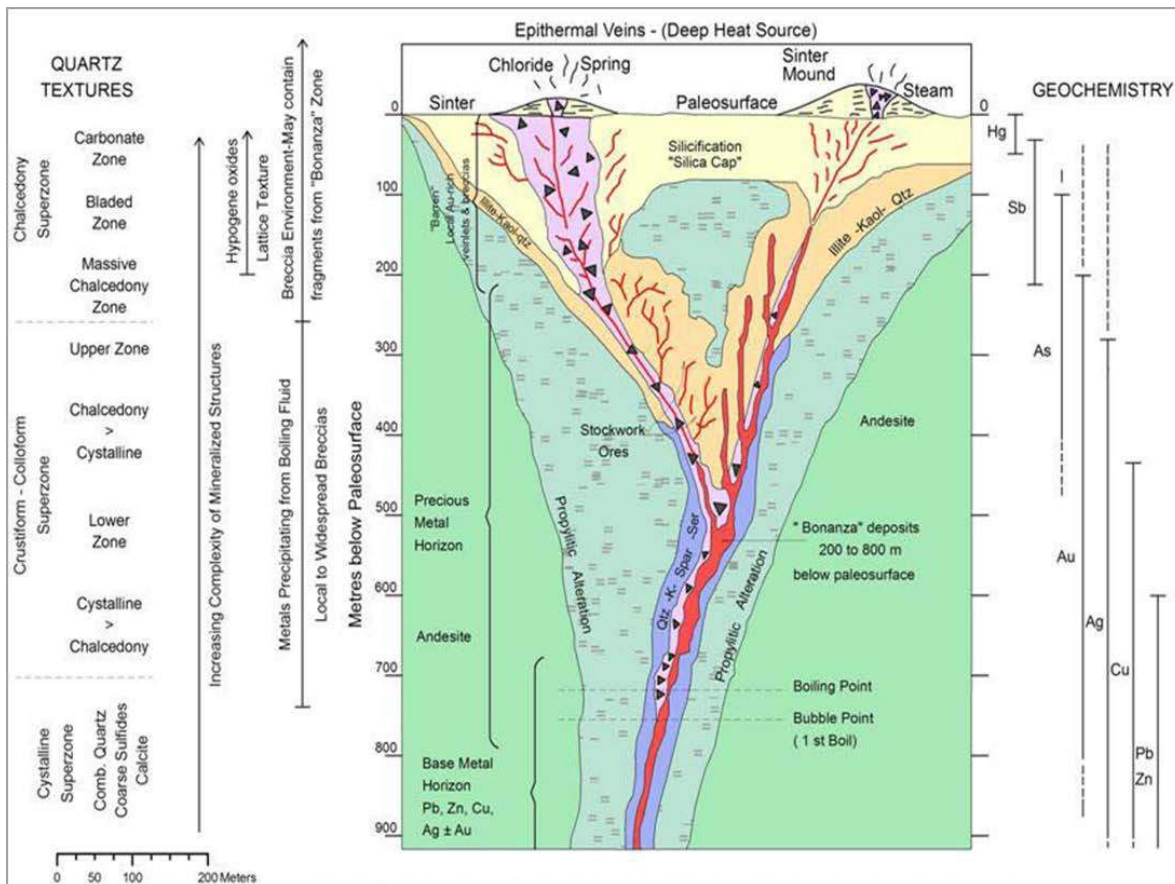


Figure 8- 1 Schematic cross section showing the key geologic elements of the main epithermal systems and their crustal depths of emplacement. After Buchanan, 1981.

9. EXPLORATION

Exploration at San Martin is concentrated along the strike length of the breccia zone. In-house diamond drilling initially tests selected targets, which is followed by underground development that outlines Mineral Reserves. Target selection is assisted by structural, geochemical and geophysical surveying that has included magnetics, induced polarization and resistivity. The resistivity surveys have been particularly successful in outlining the quartz breccia and several promising resistivity anomalies, detected since 1998, to the northeast remain to be tested. The most recent discovery at San Martin is Cuerpo 30 and 31. Extension of the structure with Cuerpo 32, 33 and 34 remain still to be tested with deep holes.

Other targets that have been drilled is the Santa Elena vein projection, to the NE of the San Martin oreshoot. This particularly structure has significant geologic potential and may represent an exceptional target for testing. The discovery of the SAM, Guadalupe and San Martin footwall veins are examples of significant recent success from the ongoing underground exploration programs.

A surface geological mapping and sampling was conducted by SIM at San Martín focused, from north to northeast structures of Chicarrama and other veins that may have some importance for exploration. Santa Elena is one of the veins that has been intercepted with surface diamond drill holes, to the NE of the San Martin Body and is exposed at coordinates 397,350E and 2,292,494N

at an elevation of 2041 m.a.s.l. The structure here consists in a breccia formed of first stages quartz and limestone fragments of all different sizes. Old trench works done by Luismin in early 90's have been cleaned and are ready for sampling. The idea that the structure was N-S trending encouraged Luismin to drill in the area, but holes, in QP opinion, were done parallel to the structure. Figure 9-1 shows a geological map of the San Martin mine with the structure of San Martin trending NE and then bending to the NW and the structure of Santa Elena shown to the NE of the San Martin body and to the SW of the tailings dam and mill.

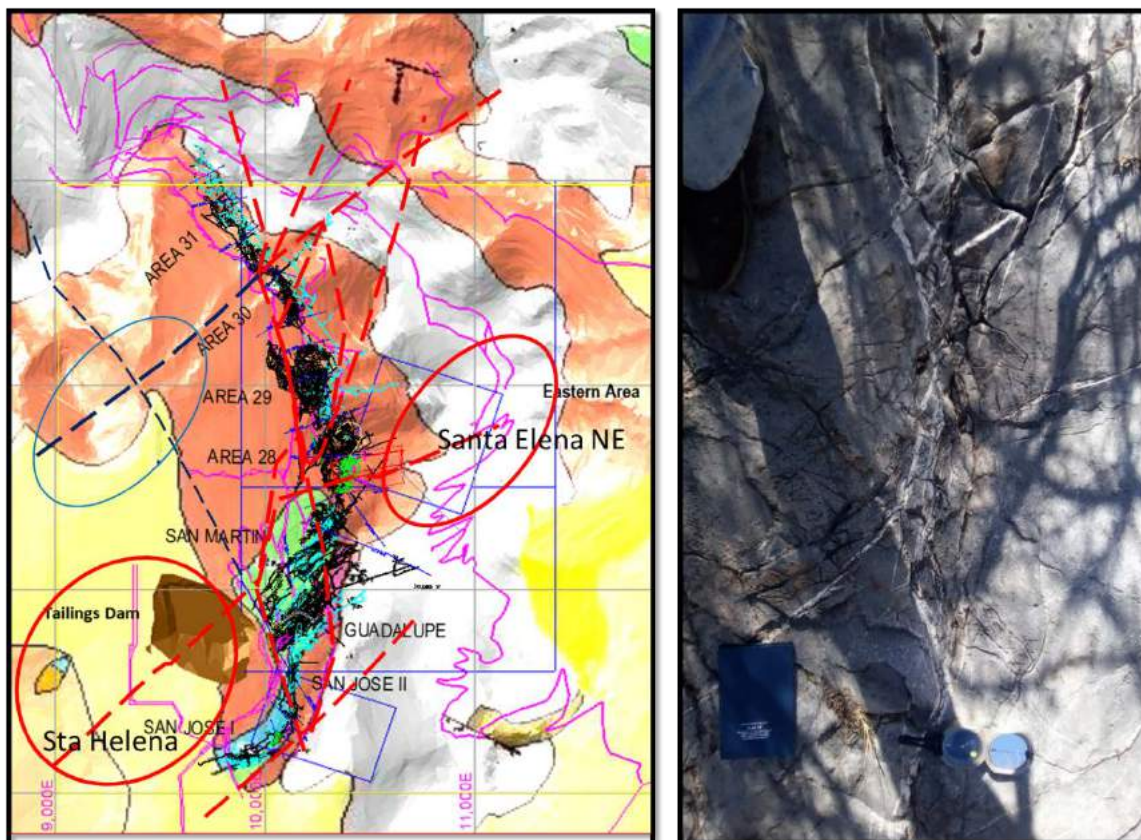


Figure 9- 1 On the left that geologic map of the district showing the San Martin structure and the Santa Elena vein, to the NE and SW. On the right, a microstructure on the Soyatal Formation that is a mirror of the major structure of San Martin. Source: CMPB Geology Department.

One sample collected recently from ant nest in the breccia, run 0.15 g/g Au and 5.2 g/t Ag. Sampling of trenches and later drilling will be necessary for exploring the Santa Elena structure, on the SW little valley.

10. DRILLING

Diamond drilling at the San Martin Mine Project is conducted under two general modes of operation: one by the exploration staff (surface exploration drilling) and the other by the mine staff (production and underground exploration drilling). Production drilling is predominantly concerned with definition and extension of the known mineralized zones in order to guide development and mining. Exploration drilling is conducted further from the active mining area

with the goal of expanding the resource base. Drilling results from both programs were not used in the mineral resource and mineral reserve estimates presented in this report. To date, all drilling completed at the mine has been diamond core.

Surface drillholes are generally oriented to intersect the veins as close to perpendicular as possible. The drillholes are typically drilled from the hanging wall, perpendicular to, and passing through the target structure into the footwall, and no drilling is designed for intercepts with angles less than about 30° to the target.

Underground drillholes are typically drilled from the hanging wall of the main structure, and are ideally drilled perpendicular to structures, but oblique intersection is required in some instances due to limitations of the drill station. All holes are designed to pass through the target and into the footwalls. Both surface and underground drillholes are typically HQ to NQ in size.

As the core is received at the core facility, geotechnical data is logged manually on paper sheets and entered to Excel. The core is then manually logged for geological data and marked for sampling. Geological data and sample information are entered directly into Excel spreadsheets.

11. SAMPLE PREPARATION, ANALYSES AND SECURITY

The samples received in the laboratory are dried before entering the preparation process. A primary size reduction is made up to 1/8 inch. The sample is divided into smaller portions using a Jones crusher until a sample of 150 g is obtained, which is considered representative of the initial sample volume.

The sample is reduced in size in a ring sprayer to a size smaller than 150 meshes, then is homogenized and placed in an envelope previously labeled with the folio number given by the Department of Geology, including the date.

From the sample in the envelope, 20 g are taken and homogenized with the mixture of fluxes to be cast and obtain the lead button that has captured the gold and silver values. This button with values is placed in a cup to remove the lead and obtain a gold and silver button at the end of the process.

The button of gold is weighed, and a chemical attack is made to dissolve the silver, the residue is pure gold that is weighed and, in this way, obtain the gold and silver grades present in the mineral sample.

This analysis of gold and silver in mineral samples has a detection limit of 0.1 g/t Au and 3.0 g/t Ag.

CMPB's internal QAQC includes adding one duplicate, one reference and one blank to every 20 samples. A sample of sterile (white) material is crushed before starting the size reduction process. The degree of reduction is verified by passing the total of the sample through the # 6 mesh; 80% of the sample must pass, otherwise the breaker opening is adjusted. This process is done in the first sample and then every 20 samples. Similarly, every 20 samples in the crusher will pass a sample of sterile material, in addition to cleaning the equipment with compressed air, including the Jones quartz that is used to divide the sample into small portions.

Continuing with the reduction process, after passing the sample through the ring sprayer, it passes through the 150 mesh, through which 80% of the total weight must pass. To avoid

contamination, compressed air is used to clean the equipment and every 20 samples a sterile material is sprayed.

The pulverized sample is taken to furnace in batches of 42 samples each. At the beginning of each batch a blank is placed, in the position number 21 a standard of known value is placed and in the position number 42 a duplicate of the sample corresponding to the position number 22 is placed.

The Assay Standard CDN-ME-1304 certified standard is from the CDN Resource Laboratories LTD laboratory, with a grade of 1.80 g/t Au and 34.0 g/t Ag. In the same way, an in-home made and validated standard is used on site, with a grade of 1.93 g/t Au and 40.5 g/t Ag.

When performing the gold and silver test and the relationship between these two elements is less than 4, it is considered to repeat the assay of the sample by adding silver nitrate (inaccurate) to increase the ratio and prevent the encapsulation of the silver.

The third-party laboratory that has been used is ALS Geochemistry, located in Guadalajara, Jalisco, of ALS Global.

In the past, personnel of Inspectorate laboratories in Vancouver has inspected the mine lab facilities and has provided procedures, flux recipes and feedback on all laboratory equipment. The mine has been awarded the Mexican Quality Award which is like International Standards ISO 9001 for quality control in the overall mining operations and with the award Certificate of Clean Industry by SEMARNAT.

12. DATA VERIFICATION

The mineral resource estimate presented in report Section 14 is based on the following information provided to Mr. Enriquez by SIM with an effective date of April 30, 2018:

- Discussions with SIM personnel;
- Personal investigation of the San Martin Mine Project office;
- An underground database received as .xls files;
- Production channel sample database (canales) revised on June 13, 2018;
- Modeled blocks for veins San José, San José II, San Martin, Cuerpo 28, Cuerpo 29, Cuerpo 30 and Cuerpo 31, 4-700;
- Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2014 and authored by Gunning, D. R. and Campbell;
- Polygonal 2-dimensional long sections for veins San José, San Martin, Cuerpo 28, and Cuerpo 29 with resource and reserve calculations.

The on-site laboratory (PENBER Lab) has undergone numerous improvements since SMI took over management of the operation in February 2008. Comparison of the on-site laboratory to commercial laboratories is conducted on an ongoing basis. The results of this analysis are presented in the July 1, 2009 NI43-101 report and for both gold and silver the variability of results were acceptable for a producing mine, thus supporting confidence in the results of the on-site lab. No other verification has been done since then.

Historically (since 1993 to 2003), the San Martin mine has been using a specific gravity of 2.7 to convert volume in cubic metres to metric tons (the tonnage factor). Under suggestion of Mr. Gunning and M. Whiting, the geological staff started to implement, a specific gravity testing procedure on diamond drill core.

Following an examination of drill core and wallrock conditions in stopes, the “Method of Archimedes” (dry mass in grams divided by water displacement in milliliters method) was chosen as a reasonable and time effective procedure. There is not a significant amount of void space, so the costlier and time-consuming methods of pre-coating drill core are not recommended.

A selection of drill core from the San Martin and Guadalupe veins was tested and a new specific gravity was recommended. The new SG is 2.55 g/cm³ was used prior 2014 Resource and Reserves. Subsequent testing more recently has shown values between 2.6 and 2.8. These new data have resulted in the use of 2.6 g/cm³ for estimates in 2014 and later.

13. MINERAL PROCESSING AND METALLURGICAL TESTING

13.1 Process of the Benefit Plant

The facilities of the plant are designed to process gold and silver ore at a rate of 850 tpd, with the capacity of 1,100 tpd, in a series circuit that includes crushing, milling, leaching, a system of countercurrent washing by decantation and Merrill Crowe for the recovery of the values.


The flow diagram of the plant consists of the following processes:

- Crushing and transport
- Storage and claim
- Primary and secondary milling
- Dynamic leaching with gaseous oxygen injection
- Counter-current washing circuit by decanting
- Precipitation of values (Merrill Crowe)
- Precipitate drying
- Refinery
- Filtering of tailings
- Storage of dry tailings
- Reagent preparation systems and their distribution

In the crushing area, the ore is reduced to ¼ in., To be fed to the primary ball mills and later to the secondary vertical mill to obtain a 70% product at 74 microns. This is fed to the dynamic leaching circuit where oxygen is injected. The dissolved values are recovered by precipitating them with zinc powder in the Merrill Crowe process and melting to obtain doré bars with a purity of 92%.

The tailings are filtered before being deposited in the area of the dam. The recovered solution is returned to the process.

A simplified block diagram of the process is shown below:

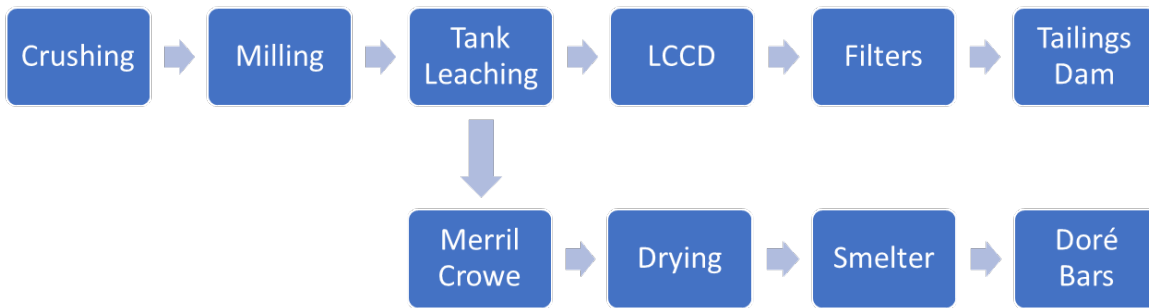

The filtered tailings are transported to the deposit to be stored, a tailing banding system is used to be compacted and wind erosion is minimized. Later, when one side of the slope is formed, reforestation with flora of the region is carried out to avoid rain erosion.

In mid-2012, a decrease in mill recoveries was detected. The problem was that carbonaceous mineral was being fed in high quantities and the recovery of gold fell 75.2% and 60.5% in the months of June and July respectively. The metallurgical investigations indicated that the ore could be recovered with the following treatment:

- a) A low temperature roast of the carbonaceous ore
- b) A conversion to Carbon in Leach processing

The organic matter in the carbonaceous mineral affects the leaching process, however, this type of mineral has always existed in the San Martin body and in the body 29 and its exploitation never caused problems in the chemical treatment in the past. This mineral was fed to the mill between 10% and 15% of the total daily processed mineral, between the years 1998 and 2003. A processing flow sheet dated April 2018 is presented in Figure 13.1.

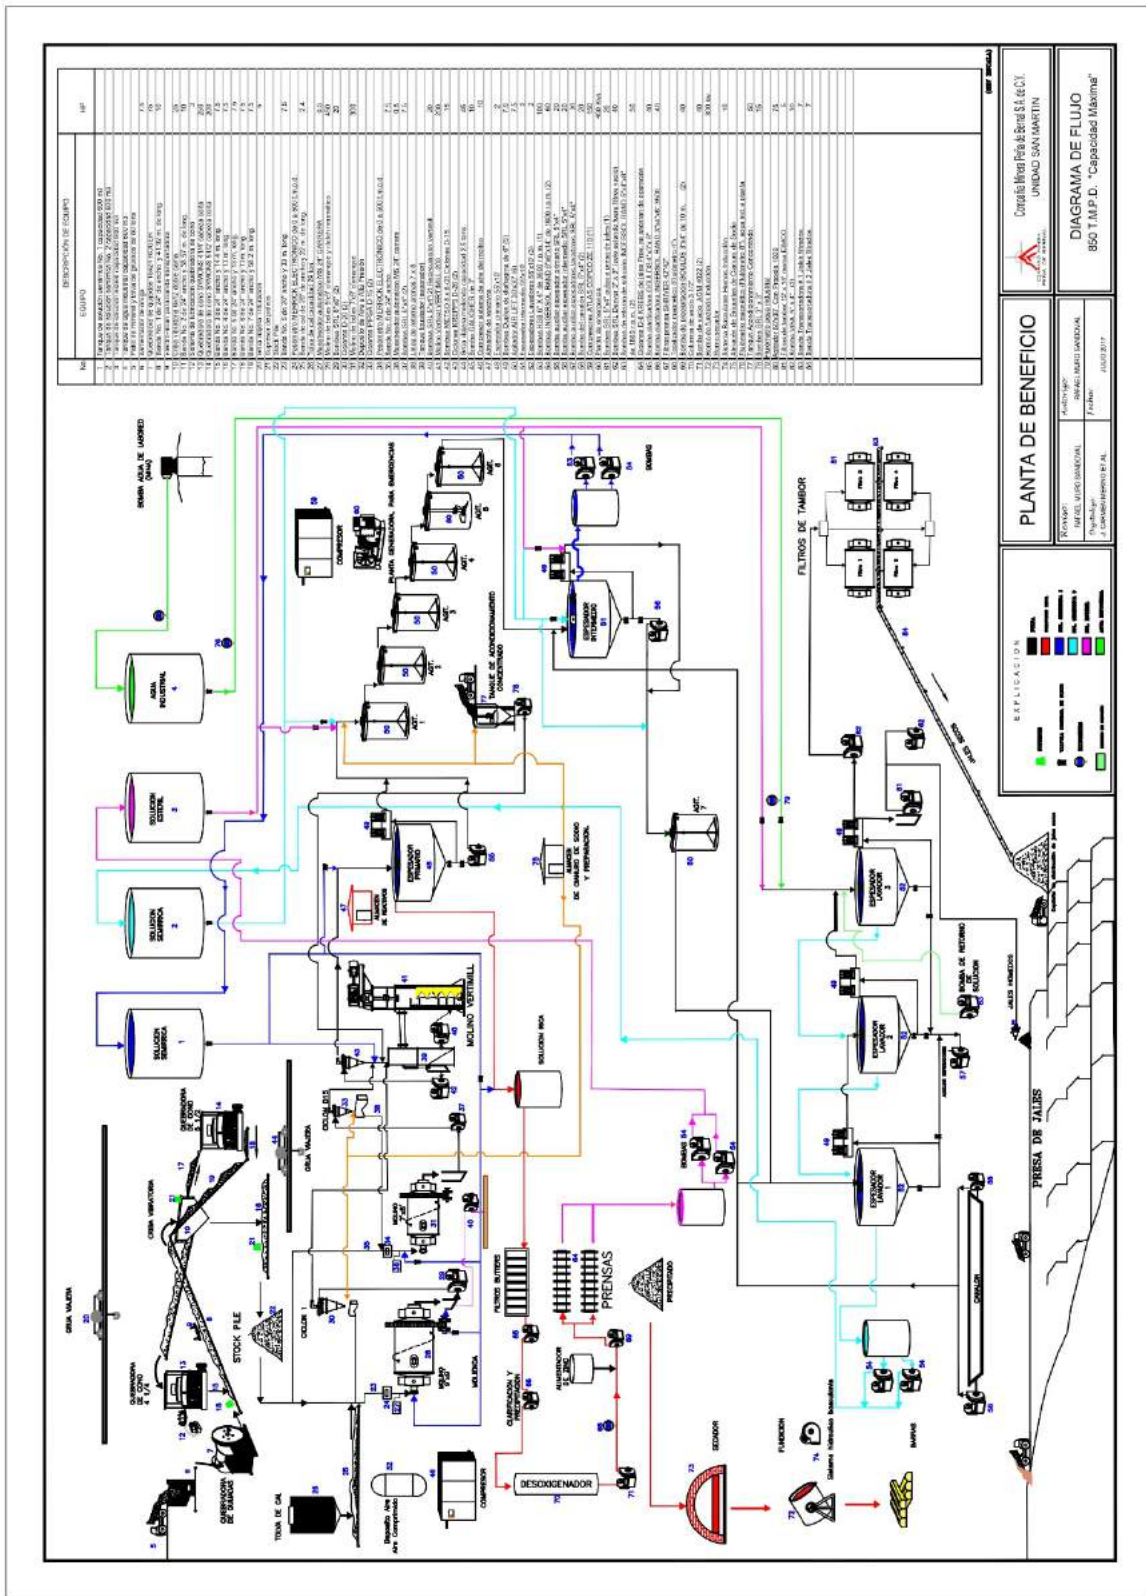


Figure 13- 1 Flowsheet of the mill process at San Martin Mine Project

14. MINERAL RESOURCE ESTIMATES

14.1 Introduction

Mr. Enriquez worked for Luismin (former owner of San Martin) for 21 years and visited the San Martin Mine regularly every other month from 1996 to 2002 and is familiarized with the deposit. Mr. Enriquez is a Qualified Person as defined by National Instrument 43-101 and has visited the San Martin Mine from June 12 to 15, 2018. Mr. Enriquez is an independent Qualified Person as defined by National Instrument 43-101. This Mineral Resource/Reserve estimate is effective as of April 30, 2018 and follows the previous independent Resource/reserve estimate performed as of July 31, 2013 and 2014 by David R. Gunning, P. Eng. and Joseph W. Campbell, P. Geo. Previous audits of Luismin's operations as of December 31, 2001; December 31, 2002; and, August 31, 2004 were performed by Watts Griffis McOuat. Prior to 2001, Pincock, Allen & Holt had conducted independent audits in the years 1998, 1999 and 2000.

Total Estimated Inferred and Indicated Resources at the San Martín Mine Project are **1,495,812 tonnes at a grade of 1.94 g Au/t and 25 g Ag/t**. The calculation of resources had not been done since 2014, when only the inferred resources were reported and not the indicated resources, not measured resources. In this Report, the inferred and indicated resources have been included, so the calculation, compared to the year 2014, increases substantially.

14.2 Density

The San Martin staff apply a factor of 2.6 tonnes/m³ to convert volume to tonnage. This is considered reasonable for the type of deposit and is based on long production experience and historic measurements.

14.3 Methodology

The Inferred and Indicated Mineral Resources are estimated by projecting typical structural geometry within the confines of the various geological structures into untested areas. The thickness of the structure and the gold and silver grades assigned to these resources was previously based on the average of past production stopes within similar structures within each mine area.

In 2010 a change was made to reflect grades from stopes that are proximal to the Inferred blocks. This resulted in a significant decrease in the grade of metals for the Inferred ore at that time but better reflects the reality of the structures. In some cases, when there are various blocks below or above the block of the projected Inferred Mineral Resources, the average of their grade and thickness is used in the estimate. However, in other cases, statistics for gold and silver that have been produced through diamond drillholes and through development are applied. Blocks for Inferred Resources are colored blue.

Indicated Mineral Reserves are defined primarily by diamond drilling. In these cases, a square is drawn on the vertical longitudinal section with the drillhole centered on the square. The shape and size of the block depends upon the geological interpretation with the maximum size of the block based on the thickness of the vein as follows:

Vein Thickness	Size of Block
Less than 1.0 m	25 x 25 m
1.0 to 1.5 m	34 x 35 m
Greater than 1.5 m	50 x 50 m

All blocks for this category are colored green.

Inferred and Indicated Mineral Resources are shown in Table 14-1

**Table 14- 1 Inferred and Indicated Mineral Resources at the San Martín Mine
Compañía Minera Peña de Bernal, SA de CV
Mineral Resource Estimate
(as of April 30, 2018)**

Mine	Tonnes	Grade		Total Contained oz		
		(Au g/t)	(Ag g/t)	(oz Au)	(oz Ag)	(oz Au Eq)
San Jose II						
Inferred	178,871	1.73	10	9,935	57,578	9,579
San Martín						
Inferred	454,288	1.82	11	26,563	153,528	25,607
Inferred	410,400	1.76	16	23,289	206,350	23,245
Retaques SM						
Inferred	20,209	1.80	13	1,170	8,447	1,146
Cuerpo 28						
Inferred	182,684	2.44	88	20,666	513,925	26,991
4-700						
Inferred	92,918	1.77	36	5,295	108,115	5,963
Total Inferred	1,339,370	1.87	24	86,917	1,047,943	99,814
San Martín						
Indicated	156,442	2.56	27	12,883	136,711	13,109
Total Indicated	156,442	2.56	27	12,883	136,711	13,109
Total Inferred + Indicated	1,495,812	1.94	25	99,800	1,184,654	112,924

- Resources are valid as of April 30, 2018 as defined by end of month April 2018 topography.
- Measured, Indicated and Inferred resource cut-off grades were 1.66 g/t gold equivalent at San Martín.
- Mineral resources are not mineral reserves and do not have demonstrated economic viability. There is no certainty that all or any part of the mineral resources estimated will be converted into mineral reserves.
- Metallurgical recoveries were 88% gold and 55% silver.
- Gold equivalents are based on a 1:81 gold: silver ratio. Au Eq= gAu/t + (gAg/t ÷ 81)

- Price assumptions are \$1300 per ounce for gold and \$16.00 per ounce for silver for resource cutoff calculations.
- Mineral resources are estimated exclusive of and in addition to mineral reserves.
- Resources are constrained by a conceptual underground mining using parameters summarized in section.
- Resources were estimated by SIM and reviewed by Erme Enriquez CPG.
- Mineral Resources that are not Mineral Reserves do not have demonstrated economic viability.

15.0 MINERAL RESERVE ESTIMATES

15.1 Introduction

Total Proven and Probable Mineral Reserves at the San Martin mine as of April 30, 2018 estimated by mine staff and reviewed by Erme Enriquez CPG, are **1,651,318 tonnes at a grade of 2.11 g Au/t and 33 g Ag/t (Table 15-1)**. This total includes Proven reserves of 409,879 tonnes grading 2.57 g/t Au and 60 g/t Ag along with Probable reserves of 1,241,439 tonnes grading 1.96 g/t Au and 24 g/t Ag. The Carbonaceous material has been included in the Reserves. The carbonaceous reserves have been always present in the deposit and has been mined and sent to the plant using normal treatment without problem. The reserves represent only 5.5% of total reserves and can be feed to the mill in small portions, as has been made in the past. There exists sufficient non- carbonaceous ore to operate for two full years, which should be enough for feeding the plant for several years.

The estimation methods used Luismin/Goldcorp have been retained to some degree, but there have been substantial changes to determination criteria for Proven and Probable reserves, and changes to dilution rates to account for the mining of Tronco ore zones and remnant ore (both hanging wall and strike and dip extensions) versus the dominance of Manto ore mined in the past.

Relative to the Manto ore the Tronco ore is thinner and steeper dipping which has resulted in higher dilution during mining due to most of the ore being mined by cut and fill methods versus the room and pillar method in the thicker flat lying Mantos. For remnant ore there is a greater dilution associated with minimal widths for mechanical equipment, which at times exceeds the remnant ore widths. There is also additional dilution associated with breaking and mucking ore next to unconsolidated fill from past mining. Cutting of some high-grade samples has been implemented to try to better predict mined grades. As well grades were lowered in some ore blocks with sufficient production history to establish the lower grades.

Modifications have also been made to the determination of Probable and Proven ore. Most notably Proven ore is only calculated for blocks above mine development, whereas in the past Proven ore was also extended below workings.

A change in 2018 to reserve estimation was made at a of the cut-off grade to 1.66 g/t gold equivalent. Th gold price of \$1300/oz used has been more or less stable in the last year compared to a price of \$1600/oz in 2012 estimate. The operating costs have reduced too, now is US\$69.41/t compared to the mining cost of US\$74 /t in 2014 estimate, resulting in a cut-off of 2.2 g/t gold equivalent.

The author believes that the Mineral Reserve and Mineral Resource estimates fairly represent the Mineral Reserve/Mineral Resource potential of the property.

The previous NI43-101 compliant estimation as of July 31, 2014 prepared by David R. Gunning, P. Eng., and Joseph W. Campbell, P. Geo, reported a total proven and probable reserves of 486,586 tonnes at a grade of 2.31 g Au/t and 18.5 g Ag/t. This total included Proven reserves of 179,589 tonnes grading 2.33 g/t Au and 17 g/t Ag along with Probable reserves of 306,997 tonnes grading 2.30 g/t Au and 19 g/t Ag. In addition to this reserve is 181,546 tonnes at a grade of 2.98 g/t Au and 32 g/t Ag which is hosted in carbonaceous limestone, of which 88,000 tonnes of this material have been mined in the last three years.

15.2 Methodology

The 2D polygonal method uses a fixed distance of Vertical Longitudinal Projection (VLP) from sample points. The VLP's are created by projecting the mine workings of a vein onto a vertical 2D long section. Figure 15-1 displays the VLP for the San José II vein. Resource blocks are constructed on the VLP based on the sample locations in the plane of the projection. SIM geologists review the data for sample trends and delineate areas with similar characteristics along the sample lines. The areas are then grouped based on mining requirements. The average grades and thicknesses of the samples are then tabulated for each block.

Resource volumes are calculated from the delineated area and the horizontal thickness of the vein, as recorded in the sample database. The volume and density are used to determine the overall resource tonnage for each area, and the grades are reported as a length weighted average of the samples inside each resource block. No special software is used for the drawing of mineral blocks on the vertical section for each of the veins.

The method of calculating proven and probable reserves is the product of many years of production in the mines operated by Luismin. This calculation system is still valid because it has worked in San Martín for the last 17 years. The calculation method of San Martín is in accordance with the parameters established by CIM.

The following criteria are used by SIM geologists to classify Proven and Probable Mineral Reserves. The distance for vertical projections for Proven Mineral Reserves and Probable Mineral Reserves is a function of the length of the block, defined as follows:

Block Length	Maximum Vertical Projection for Proven Mineral Reserves	Maximum Vertical Projection for Probable Mineral Reserves
Less than 15 m	4 m	8 m
15 to 45 m	8 m	16 m
45 to 85 m	16 m	32 m
Greater than 85 m	20 m	40 m

Longitudinal sections and plans showing the Proven and Probable Reserves and the Inferred Mineral Resources are shown in appendix III.

15.3 Definitions

The mineral resource estimation for the San Martin Mine was completed in accordance to the guidelines of Canadian National Instrument 43-101 (“NI 43-101”). The modeling and estimation of the mineral resources were completed in June 30, 2018 under the supervision of Erme Enriquez, qualified person with respect to mineral resource estimations under NI 43-101. The effective date of the resource estimate is April 30, 2018. Mr. Enriquez is independent of SIM by the definitions and criteria set forth in NI 43-101; there is no affiliation between Mr. Enriquez and SIM except that of independent consultant/client relationships.

The San Martin resources are classified in order of increasing geological and quantitative confidence in Proven and Probable, Inferred, Indicated, and Measured categories in accordance with the “CIM Definition Standards – For Mineral Resources and Mineral Reserves” (2014) and therefore NI 43-101. CIM mineral resource definitions are given below, with CIM’s explanatory text shown in italics:

Mineral Resource

Mineral Resources are sub-divided, in order of increasing geological confidence, into Inferred, Indicated and Measured categories. An Inferred Mineral Resource has a lower level of confidence than that applied to an Indicated Mineral Resource. An Indicated Mineral Resource has a higher level of confidence than an Inferred Mineral Resource but has a lower level of confidence than a Measured Mineral Resource.

A Mineral Resource is a concentration or occurrence of solid material of economic interest in or on the Earth’s crust in such form, grade or quality and quantity that there are reasonable prospects for eventual economic extraction. The location, quantity, grade or quality, continuity and other geological characteristics of a Mineral Resource are known, estimated or interpreted from specific geological evidence and knowledge, including sampling.

Material of economic interest refers to diamonds, natural solid inorganic material, or natural solid fossilized organic material including base and precious metals, coal, and industrial minerals.

The term Mineral Resource covers mineralization and natural material of intrinsic economic interest which has been identified and estimated through exploration and sampling and within which Mineral Reserves may subsequently be defined by the consideration and application of Modifying Factors. The phrase ‘reasonable prospects for eventual economic extraction’ implies a judgment by the Qualified Person in respect of the technical and economic factors likely to influence the prospect of economic extraction. The Qualified Person should consider and clearly state the basis for determining that the material has reasonable prospects for eventual economic

extraction. Assumptions should include estimates of cutoff grade and geological continuity at the selected cut-off, metallurgical recovery, smelter payments, commodity price or product value, mining and processing method and mining, processing and general and administrative costs. The Qualified Person should state if the assessment is based on any direct evidence and testing.

Interpretation of the word ‘eventual’ in this context may vary depending on the commodity or mineral involved. For example, for some coal, iron, potash deposits and other bulk minerals or commodities, it may be reasonable to envisage ‘eventual economic extraction’ as covering time periods in excess of 50 years. However, for many gold deposits, application of the concept would normally be restricted to perhaps 10 to 15 years, and frequently to much shorter periods of time.

Inferred Mineral Resource

An Inferred Mineral Resource is that part of a Mineral Resource for which quantity and grade or quality are estimated on the basis of limited geological evidence and sampling. Geological evidence is sufficient to imply but not verify geological and grade or quality continuity. An Inferred Mineral Resource has a lower level of confidence than that applying to an Indicated Mineral Resource and must not be converted to a Mineral Reserve. It is reasonably expected that the majority of Inferred Mineral Resources could be upgraded to Indicated Mineral Resources with continued exploration.

An Inferred Mineral Resource is based on limited information and sampling gathered through appropriate sampling techniques from locations such as outcrops, trenches, pits, workings and drill holes. Inferred Mineral Resources must not be included in the economic analysis, production schedules, or estimated mine life in publicly disclosed Pre-Feasibility or Feasibility Studies, or in the Life of Mine plans and cash flow models of developed mines. Inferred Mineral Resources can only be used in economic studies as provided under NI 43-101.

There may be circumstances, where appropriate sampling, testing, and other measurements are sufficient to demonstrate data integrity, geological and grade/quality continuity of a Measured or Indicated Mineral Resource, however, quality assurance and quality control, or other information may not meet all industry norms for the disclosure of an Indicated or Measured Mineral Resource. Under these circumstances, it may be reasonable for

the Qualified Person to report an Inferred Mineral Resource if the Qualified Person has taken steps to verify the information meets the requirements of an Inferred Mineral Resource.

Indicated Mineral Resource

An Indicated Mineral Resource is that part of a Mineral Resource for which quantity, grade or quality, densities, shape and physical characteristics are estimated with sufficient confidence to allow the application of Modifying Factors in sufficient detail to support mine planning and evaluation of the economic viability of the deposit.

Geological evidence is derived from adequately detailed and reliable exploration, sampling and testing and is sufficient to assume geological and grade or quality continuity between points of observation.

An Indicated Mineral Resource has a lower level of confidence than that applying to a Measured Mineral Resource and may only be converted to a Probable Mineral Reserve. Mineralization may be classified as an Indicated Mineral Resource by the Qualified Person when the nature, quality, quantity and distribution of data are such as to allow confident interpretation of the geological framework and to reasonably assume the continuity of mineralization. The Qualified Person must recognize the importance of the Indicated Mineral Resource category to the advancement of the feasibility of the project. An Indicated Mineral Resource estimate is of sufficient quality to support a Pre-Feasibility Study which can serve as the basis for major development decisions.

Measured Mineral Resource

A Measured Mineral Resource is that part of a Mineral Resource for which quantity, grade or quality, densities, shape, and physical characteristics are estimated with confidence sufficient to allow the application of Modifying Factors to support detailed mine planning and final evaluation of the economic viability of the deposit.

Geological evidence is derived from detailed and reliable exploration, sampling and testing and is sufficient to confirm geological and grade or quality continuity between points of observation. A Measured Mineral Resource has a higher level of confidence than that applying to either an Indicated Mineral Resource or an Inferred Mineral Resource. It may be converted to a Proven Mineral Reserve or to a Probable Mineral Reserve.

Mineralization or other natural material of economic interest may be classified as a Measured Mineral Resource by the Qualified Person when the nature, quality, quantity and distribution of data are such that the tonnage and grade or quality of the mineralization can be estimated to within close limits and that variation from the estimate would not significantly affect potential economic viability of the deposit. This category requires a high level of confidence in, and understanding of, the geology and controls of the mineral deposit.

Modifying Factors

Modifying Factors are considerations used to convert Mineral Resources to Mineral Reserves. These include, but are not restricted to, mining, processing, metallurgical, infrastructure, economic, marketing, legal, environmental, social and governmental factors.

15.4 Reconciliation of Mineral Reserves to Production

Due to the lack of data for calculating reserves and reconciling resources, the transformation of resources into reserves was used for this purpose. This method was established by Mr. Enriquez, for all Luismin's operations, and was used by WGM for their Technical Report of 2009.

The Transformation of resources into reserves, for the period of April 2014 to April 2018 is shown in Table 15-1. QP states that the data used for this report, where the transformation of inferred resources into proven and probable reserves is calculated, has the same validity as those used in the past by Luismin, and with which it was operated for a long period of time.

During the four-year period (2014 to 2017), the percentage of the estimated Inferred Resource at San Martin transformed into Mineral Reserves was 216% (i.e. the Inferred Mineral Resource was under estimated as the estimate transformed into Mineral Reserves was exceeded by 116%. This is right since no indicated resources have been determined in the history of the deposit.

Table 15- 1 Resources transformed into reserves from Apr 2014 to Apr 2018

Starcore International Mines LTD
Compañía Minera Peña de Bernal, SA de CV
Resources Transformed into Reserves
April 30 2014 to April 30 2018

Area	Inferred Resources 2014			Production Apr-2014 to Apr 2018			Reserves Apr 2018			Production+ Reserves	Transf %
	Tonnes	Au (g/t)	Ag (g/t)	Tonnes	Au (g/t)	Ag (g/t)	Tonnes	Au (g/t)	Ag (g/t)		
San José I	73,510	2.22	7	3998	1.49	6	-	-	-	3998	5
San Jose II	18,900	2.31	31	50704	1.84	13	137,593	2.76	32	188297	996
San Martin	400,000	2.05	11	572056	2.10	15	349,726	2.94	26	921782	230
San Martin FW	105,058	2.78	12	-	-	-	-	-	-	-	-
Guadalupe	150,971	1.30	47	166158	2.19	13	-	-	-	166158	110
Retaques SM	-	-	-	-	-	-	20,209	1.80	13	20209	100
Cuerpo 28	59,638	2.25	22	164004	2.03	35	140,534	2.93	105	304538	511
Cuerpo 29	67,319	3.07	76	99904	2.85	42	-	-	-	99904	148
Cuerpo 30	23,405	3.30	63	88292	2.96	49	-	-	-	88292	377
4-700	-	-	-	-	-	-	146,653	1.84	43	146653	100
Total	898,801	2.15	24	1,145,117	2.22	23	794,715	2.29	36	1,939,832	216

The geology staff at San Marín prepare reconciliations of the Life of Mine plan (LOM) to actual production from sampling monthly. The reconciliation compares the LOM with geology estimates from chip sampling and plant estimates based on head grade sampling. Reconciliation estimates a positive variance on tonnes for both geology and LOM as compared to the plant reported tonnes for 2017 (Table 15-2). Estimated tonnage was 3% lower for geology and 3.1% lower for the plant than specified in the LOM. Silver equivalent grades were 16% higher for geology and 14% lower for the plant than specified in the LOM. The differences in less tonnage and lower grades than the LOM can be attributed to lower gold prices and thus development was limited during 2017.

Table 15- 2 Mine Plant Reconciliation San Martin Mine

	LOM	GEOLOGY	PLANT
Ore Mined	277,950	269,521	269,521
Grade Au	1.92	2.18	1.58
Grade Ag	17	29	23
Grade AuEq	2.13	2.55	1.87
Ounces Au	14,441	15,994	12,351
Ounces Ag	77,441	150,850	116,627
Ounces AuEq	15,409	17,880	13,809

Although the reconciliations conducted by SMI show fair comparisons on planned values versus actual values the reconciliation process should be improved to include the estimated tonnes and grade from the resource models. By comparing the LOM plan monthly to the plant production, the actual physical location of the material mined may be different in the plan versus the actual area that was mined.

The overall reconciliation is good and supported the mine's ongoing program of reserve estimation and grade control. It has been determined since that time that neither tonnage or grade were in fact reconciled with the mill production, which has resulted in some historic production being overstated and some resource grades are also overstated. The reconciliation process needs to be improved and estimated year to year by using the normal procedures, particularly regarding resource grade which tend to be based on average production grades from similar orebodies.

15.5 Mineral Reserves

Mineral reserves are derived from Inferred resources after applying the economic parameters as stated previously and utilizing the VLP to generate stope designs for the reserve mine plan. The stope designs are then used to mine on levels along with the required development for the final mine plans. The San Martín Mine Project mineral reserves have been derived and classified according to the following criteria:

Figures 15-1 and 15-2 shows reserve blocks depicted on a portion of a typical longitudinal section. Proven reserve blocks are shown in red, Probable reserve blocks are shown in yellow. The mine planners have determined that extraction of the blocks is feasible given grade, tonnes, costs, and access requirement.

The San Martín Mine Project mineral reserves have been derived and classified according to the following criteria:

- Proven mineral reserves are the economically mineable part of the Measured resource for which mining, and processing/metallurgy information and other relevant factors demonstrate that economic extraction is feasible.

- Probable mineral reserves are those Measured or Indicated mineral resource blocks which are considered economic and for which SIM has a mine plan in place.

The Proven and Probable mineral reserves for the San Martín mine as of April 30, 2018 are summarized in Table 15-3. The mineral reserves are exclusive of the mineral resources reported in Section 14 of this report.

Table 15- 3 Proven and Probable Mineral Reserves, Effective Date April 30, 2018

Compañía Minera Peña de Bernal, SA de CV
San Martín Summary of Ore Reserves
(as of April 30, 2018)

Area	Tomos	Ave. Width (m)	Grades (g/t)			Content oz	
			Au	Ag	AuEq	Au	Au Eq
San José II							
Proven	86,485	2.85	1.77	10	1.89	4,912	5,252
Probable	27,425	2.40	1.78	13	1.94	1,574	1,713
Total	113,910	2.75	1.77	11	1.90	6,486	6,965
San Martín							
Proven	27,893	2.73	2.00	9	2.11	1,791	1,889
Probable	1,035,267	3.86	1.85	13	2.01	61,632	67,026
Total	1,063,160	3.83	1.86	13	2.02	63,423	68,915
Cuerpo 28							
Proven	221,265	3.56	2.22	78	3.19	15,803	22,661
Probable	150,314	4.74	2.09	88	3.17	10,110	15,318
Total	371,579	4.04	2.17	82	3.18	25,914	37,979
Cuerpo 29							
Proven	56,354	3.56	4.58	101	5.81	8,290	10,535
Probable	17,711	3.44	4.72	138	6.42	2,688	3,658
Total	74,065	3.53	4.61	110	5.96	10,978	14,193
Cuerpo 30							
Proven	9,618	2.28	6.60	38	7.07	2,042	2,185
Probable	0	0.00	0.00	0	0.00	0	0
Total	9,618	2.28	6.60	38	7.07	2,042	2,185
Cuerpo 31							
Proven	8,264	2.16	4.03	30	4.40	1,071	1,168
Probable	10,722	2.45	5.93	41	6.43	2,045	2,218
Total	18,986	2.32	5.10	36	5.55	3,116	3,385
TOTAL							
PROVEN	409,879	3.29	2.57	60	3.32	33,910	43,690
PROBABLE	1,241,439	3.92	1.96	24	2.25	78,049	89,933
Total Proven and Probable	1,651,318	3.61	2.11	33	2.52	111,958	133,622

- Reserve cut-off grades are based on a 1.66 g/t gold equivalent.
- Metallurgical Recoveries were 88% gold and 55% silver.
- Mining Recoveries of 90% were applied.
- Minimum mining widths were 1.5 meters.
- Dilution factors is 20%. Dilution factors are calculated based on internal stope dilution calculations.
- Gold equivalents are based on a 1:81 gold:silver ratio. $Au Eq = gAu/t + (gAg/t \div 81)$
- Price assumptions are \$1300 per ounce for gold and \$16 per ounce for silver.
- Mineral resources are estimated exclusive of and in addition to mineral reserves.
- Resources were estimated by SIM and reviewed by Erme Enriquez CPG.

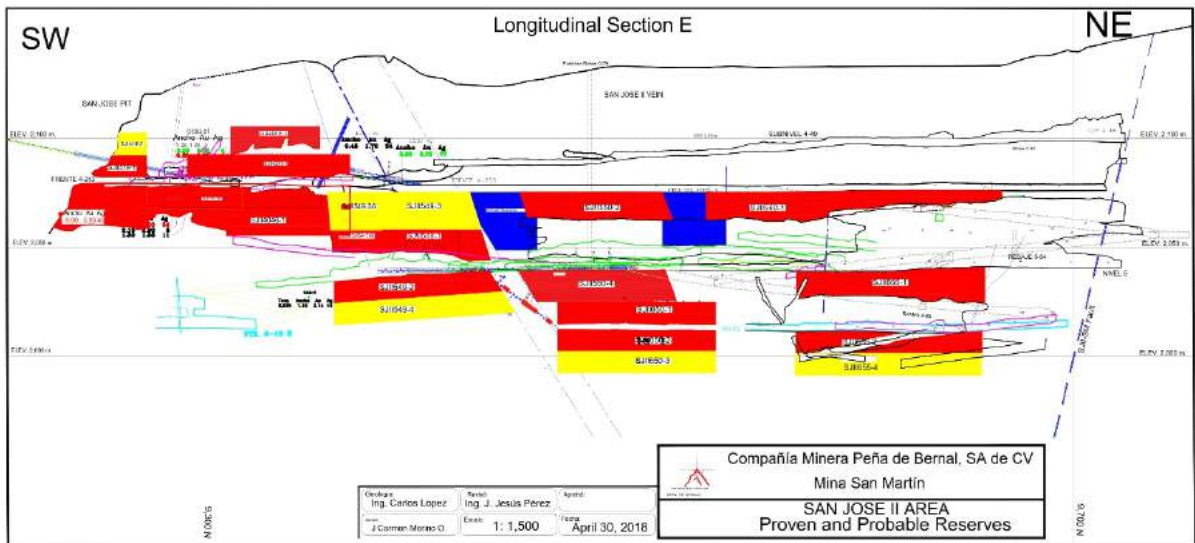


Figure 15- 1 Typical vertical longitudinal section (VLP) showing the blocks of proven and probable ore in the San José II orebody.

15.6 Factors that may affect the Reserve Calculation

The San Martín operation is an operating mine with a relatively long history of production. The mine staff possess considerable experience and knowledge with regard to the nature of the orebodies in and around the San Martín Mine Property. Mine planning and operations need to continue to assure that the rate of waste development is sufficient to maintain the production rates included in the mine plan. It is unlikely that there will be a major change in ore metallurgy during the life of the current reserves, as nearly all of the ore to be mined will come from veins with historic, recent, or current production. The process of mineral reserve estimation includes technical information which requires subsequent calculations or estimates to derive sub-totals, totals and weighted averages. Such calculations or estimations inherently involve a degree of rounding and consequently introduce a margin of error. The QP does not consider these errors to be material to the reserve estimate. Areas of uncertainty that may materially impact the Mineral Reserves presented in this report include the following:

- Mining assumptions,
- Dilution assumptions,
- Exchange rates,
- Changes in taxation or royalties,
- Variations in commodity price,
- Metallurgical recovery, and
- Processing assumptions

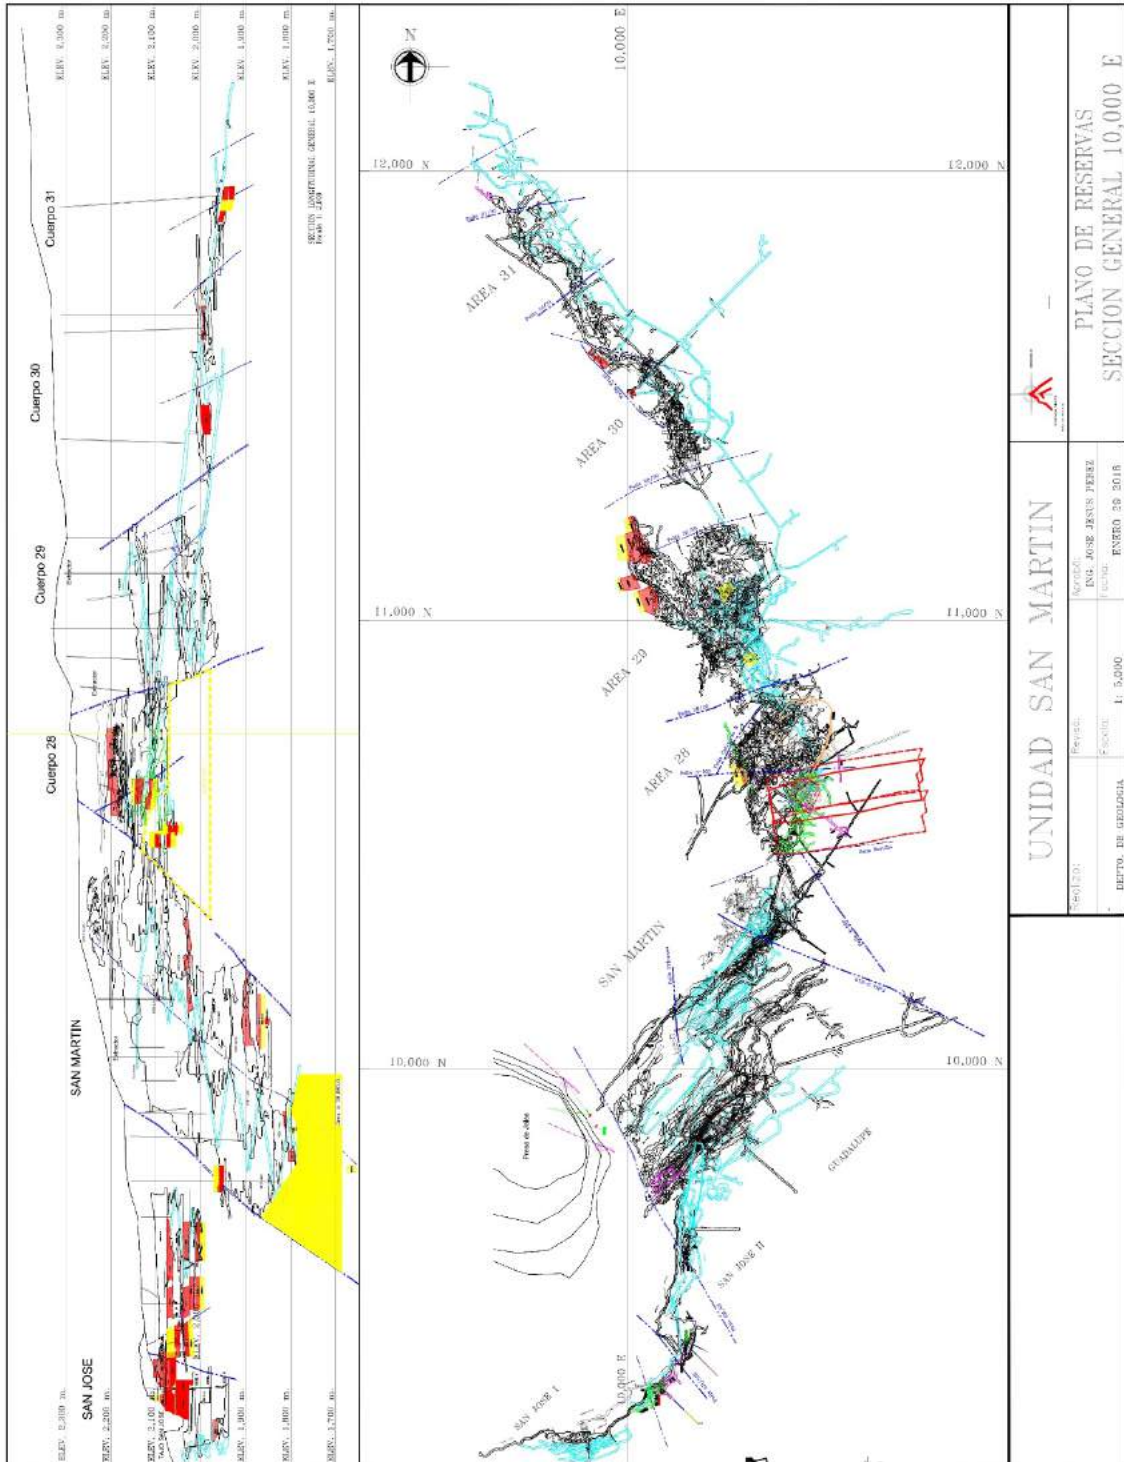


Figure 15- 2 General vertical longitudinal section of the San Martin Mine showing the proven and probable reserve blocks.

16. MINING METHODS

16.1 Mining Operations

Since 2007, SIM has been in control of the day-to-day mining operations at the San Martin Mine Project. SIM assumed control of the mining operations from a local mining contractor in order to allow for more flexibility in operations and to continue optimizing the costs.

The San Martin Mine project has a roster of 75 employees, 170 unionized workers and an additional 152 contractors. The San Jose mine operates on two 10-hour shifts (contractors) 20 by 8. The San Martin works 3 shifts 8 hours each, six days a week. The supervisors are in shifts of 20 by 8 for body 28 and 10 by 4 for San Martin. The mill operates on a 20/8 schedule.

The CMPB miners are skilled and experienced in vein mining and are currently unionized. In the production / development function, the Company's agreement with the contractor is based on a set price. There is an incentive system in place rewarding personnel for good attendance, safety and production. Technical services and overall supervision are provided by SIM staff. The mine employs geology, planning and surveying personnel and has detailed production plans and schedules. All mining activities are being conducted under the direct supervision and guidance of the mine manager.

16.2 Mining Method


The San Martin underground mine is accessed through a tunnel located at the 2,050-meter level. Underground production is conducted utilizing mechanized cut and fill stopes using dry waste as backfill. The backfill comes from development and stope preparation. Ore is hauled out of the mine by dump trucks of 14 m³.

As in many other mines, variants of mining methods are used in the San Martin mine. Following a detailed description is given that aims to clarify how to mine in this mine.


Mining Methods of exploitation used in San Martin mine, in the three sectors of the mine:

- Body 28
- San Martin Body
- San Jose Body


It is known that the exploitation of mineral deposits by underground methods is more complex than those on the surface, so it is necessary to devote special attention to each of the existing methods, for a successful planning of the exploitation of a body of ore. The selection of the mining method that is intended to be used in a deposit or a mineralized body must be studied carefully, taking into consideration that it is the method that must be adapted to the deposit and not in the opposite way.

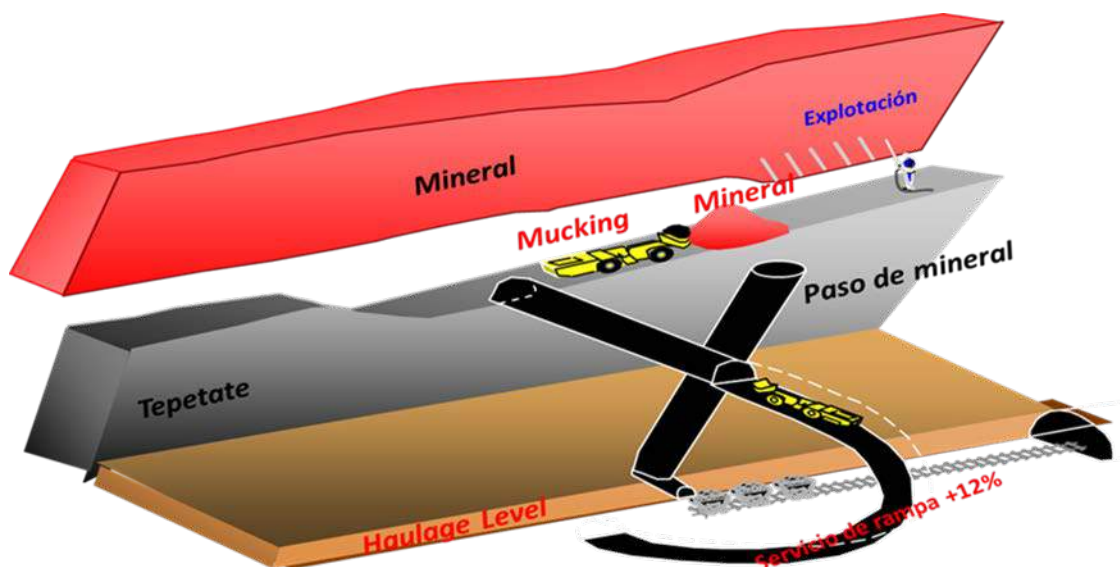

mining method, used in the stopes with tabular mineral body in vein, is Cut and Fill. In this mining method, mining is done from the bottom to the top of the different horizons or mineral floor. It consists of opening a raise on ore that will serve as a slot or exit for the blasting, semi vertical or the closest to 90°, respecting the dip of the mineralized structure. After a mineral cut has been completely extracted, respecting a previously marked line of lag, it is then filled with backfill or waste material until the control line that previously served as a reference for mucking. Before starting the new cut in the cycle, cut-extraction-filling is repeated until finished.

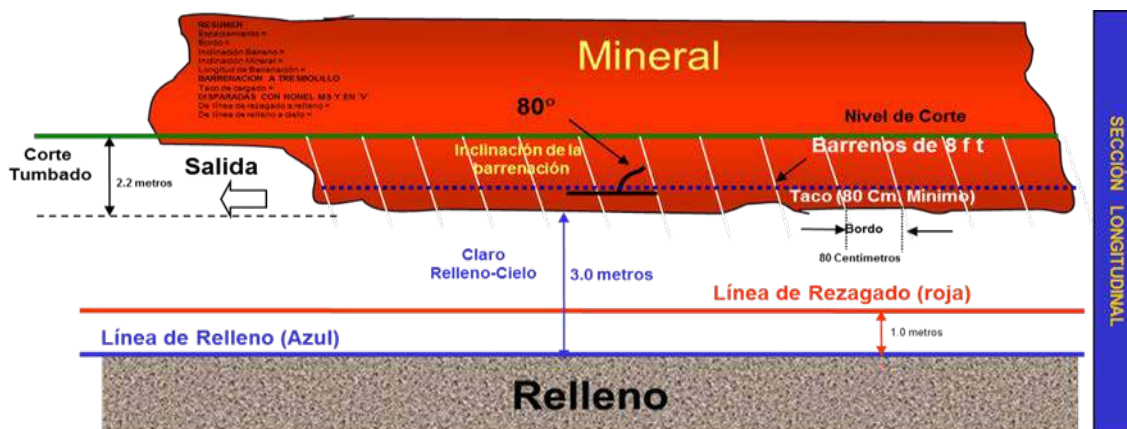

Secciones

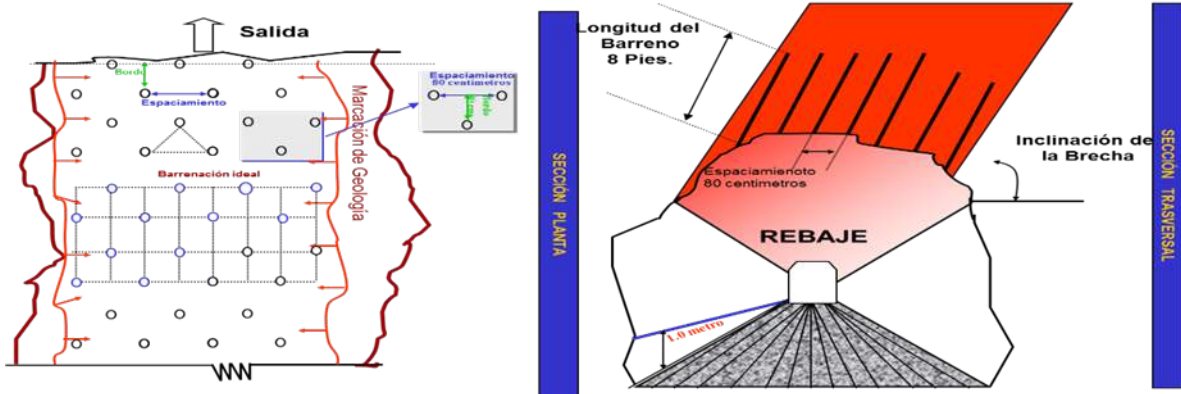


Due to the mineralization potential in the body 28, because it is a large breccia and not a tabular or vein body, two mining methods were adapted, considering first developing parallel streets, separated by 4 to 5 metre pillars, turning these streets into the primary blocks and the pillars in the secondary blocks.

Cut is done in two phases: In a first stage, shrinkage is applied to the primary blocks until reaching the upper level located at 8 to 10 metres up. In this phase the infill is done by using a type of cemented filling (CRF, Cemented Rock Fill), to give extra support to the fill. In the second phase cut and fill is used to recover the secondary blocks. The main characteristics of this mining is that a maximum recovery of ore is guaranteed, the subsidence of the land is prevented both from the surface and inside the mine and the highest possible production is maintained.

To evaluate the dimensions and stability of the stopes, modeling by finite elements and an empirical calculation of the sizing of stopes were used to evaluate mainly the stability and guarantee the safety of the area.

Conclusions for mining the body 28 were: The dimensions of the proposed stopes are up to 4-metre-wide by 8-metre-high by 20-metre-long, based on the general geomechanical characteristics of the breccia-structure and the stability of the rock mass and operational safety. When there are areas of lower quality, such as fault zones and areas of breccia with high fracturing and a poor matrix, it is necessary to use shotcrete accompanied by electro-welded mesh and cables for better support of the rock. Also, the dimensions of the stopes are reduced to avoid rock falling or dilution by the unstable walls of the stopes and to increase the safety of the mining operation.

The increase in the dimensions of the stopes is directly proportional to the use of support elements such as cables, mesh or shotcrete.

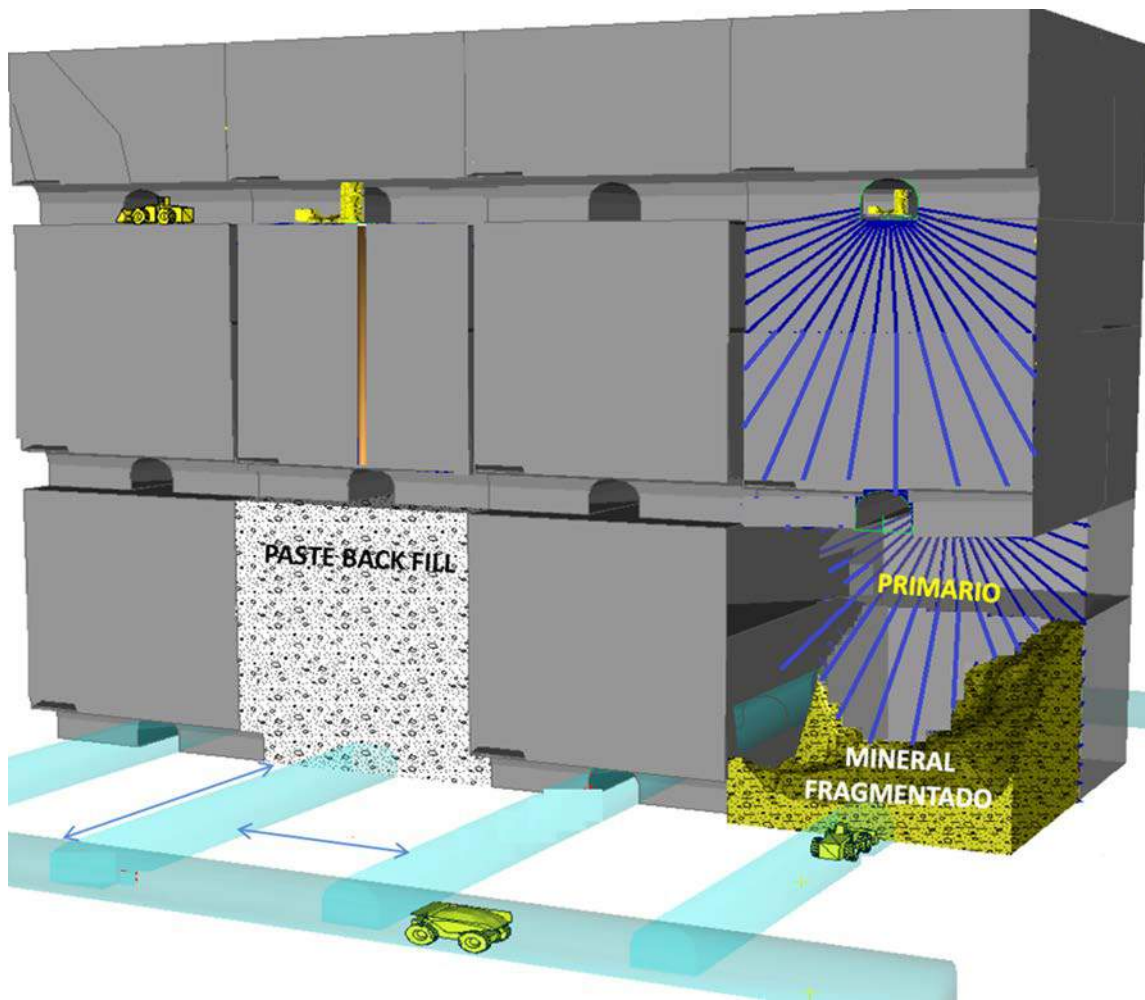


The first stage consists of the development and mining of primary streets. Drifting is carried out with jackleg drills starting with dimensions of 4.0 x 3.0 metre, both on a lower level and an upper level separated by a vertical pillar of 8 metre.

As a result, vertical cuts are made using shrinkage system for the communication of both levels and the subsequent mucking with remote-controlled scoop tram equipment. The next step is filling the open space created by this cycle, with a mixture of dry backfill, sand and 5% cement. Once the filling is completed, the following step is the development and mining of the secondary blocks:


A drift is driven with a section of 4.0 x 2.5 metres, in a single lower level. Subsequently, the cut and fill is applied in an ascending manner, with cuts of 1.8 m to avoid clearings of prolonged heights and guarantee the safety of the area.

SECCIÓN LONGITUDINAL REBAJE

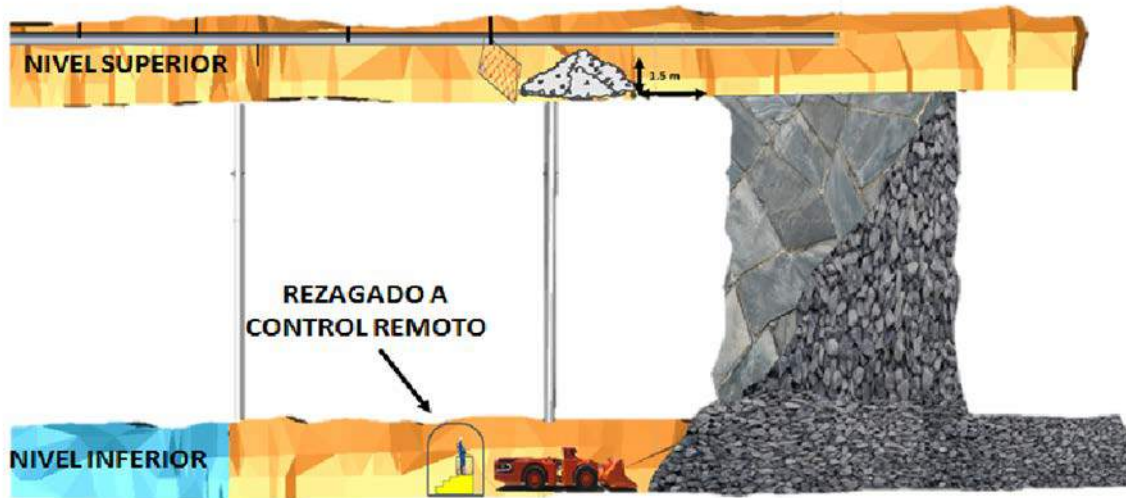

Once the stopes are empty of ore, they are filled with CRF or waste-cement filling with the support of scooptrams. The CRF mixture contains 86% waste, 5% Portland cement and 9% water, which gives us the strength ($5.0 \text{ kg} / \text{cm}^2$) and setting time of 28 days, necessary for the exploitation cycle.

The cemented filling, which is called consolidated (consolidado), of the primary blocks, is carried out in a single stage: A plug is placed in the lower level and then the CRF is emptied from the upper level, in a clearing of 8 metres high, with support from scooptram, which is accumulated in a descending way, in the form of a waterfall, until the stop is filled 100%. For the secondary streets it is used normal dry fill with waste rock.

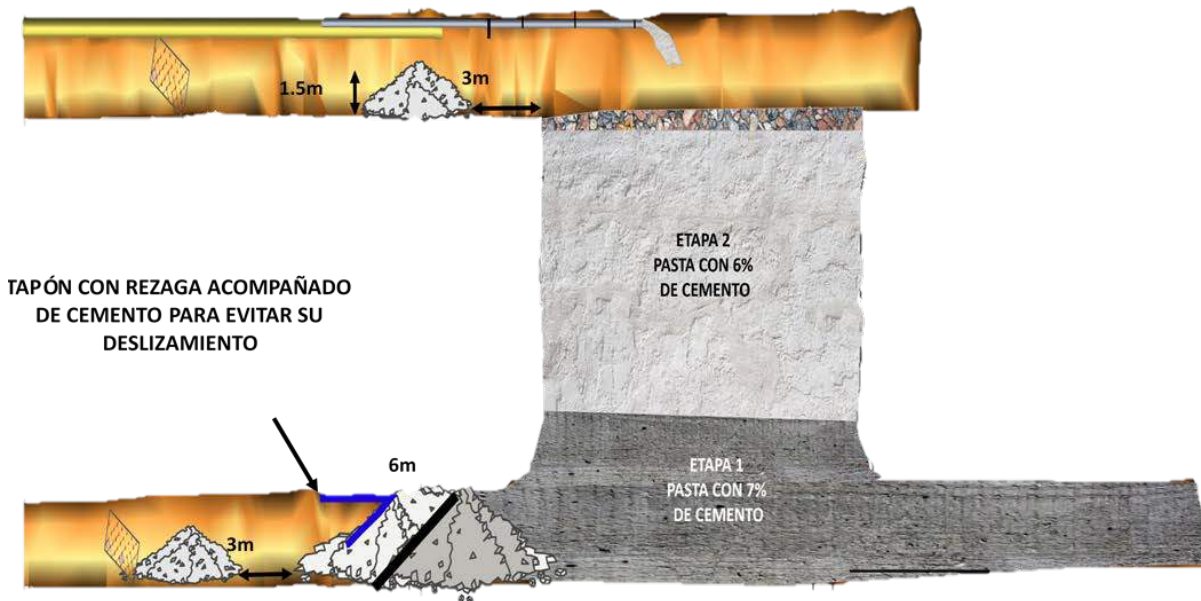

16.3 Mining Equipment

Ore and waste transportation is by scooptram and truck haulage. Ore and waste haulage is performed using 14-tonne underground trucks. Single boom jumbo drills and jacklegs are used for development headings and conventional cut and fill stope drilling is by jackleg. A total of 45 jackleg drills are available in inventory.

A list of the major underground equipment on-hand at San Martin is listed below. According to SMI's personnel, all that equipment is in good, well-maintained condition and is operating on very smooth clean roads.

Table 16- 1 SIM List of Mine Equipment in the San Martin Mine Project

Starcore International Mines LTD
Compañía Minera Peña de Bernal, SA de CV
Mining Equipment San Martin Mine

Equipment	ID Econ.	Make/Model	Capacity	Year
SCOOP TRAM	07	MTI, LT-410	3 Yds.	2000
SCOOP TRAM	15	MTI, LT-350	2.5 Yds.	2003
SCOOP TRAM	21	MTI, LT-650	4 Yds.	2014
SCOOP TRAM	22	JOY, LT-650	4 Yds.	2017
SCOOP TRAM	23	WAGNER, ST2B	2 Yds.	1988
SCOOP TRAM	24	JOY, LT-270	1.5 Yds	2016
SCOOP TRAM	25	JOY, LT-270	1.5 Yds	2017
SCOOP TRAM	26	JOY, LT-650	4 Yds.	2017
LOW PROFILE TRUCK	03	TAMROCK,	16 Tons.	2005
JUMBO	03	TAMROCK, QUASAR	14 Ft.	2003
JUMBO	07	SANDVIK DD210	8/12 Ft.	2017
AGRICULTURE TRACTOR	05	NEW HOLLAND, TT75	***	2011
AUTOHORMIGONERA	11	AUSA, 1000 RMX	1m ³	2003
ALLEN TOWN	03	PUTZMEISTER TK 20		2011
BACKHOE	01	CASE 580 SUPER M series 2 (580SM)	1.03 yd/	2013
PAYLOADER	12	THOMAS	14.3 cft	2004
TOYOTA	01	TOYOTA, ENS INDUSTRIAL (LAND CRUISER HZJ79)	***	2004
TOYOTA	02	TOYOTA, ENS INDUSTRIAL (LAND CRUISER HZJ79)	***	2004
MULE	02	KAWASAKI MULE 4010 4X4 DIESEL (KAF950FDF)	***	2016
KUBOTA	01	KUBOTA RTV-X1140W-H	***	2017
RANGER	01	POLARIS RANGER 900 DIESEL 4X4	***	2011
RANGER	02	POLARIS RANGER 900 DIESEL 4X4	***	2011
RANGER	03	POLARIS RANGER 900 DIESEL 4X4	***	2011
RANGER	04	POLARIS RANGER 900 CREW DIESEL 4X4	***	2011
NISSAN	01	NISSAN NP300 DIESEL 4X4 2012	***	2012
NISSAN	02	NISSAN NP300 DIESEL 4X4 2014	***	2014
NISSAN	03	NISSAN NP300 DIESEL 4X4 2013	***	2013
DUMP TRUCK	12	INTERNATIONAL DURASTAR 4400	14m	2012
DUMP TRUCK	14	INTERNATIONAL DURASTAR 4400	14m	2014
DUMP TRUCK	15	INTERNATIONAL DURASTAR 4400	14m	2015
DUMP TRUCK	16	INTERNATIONAL DURASTAR 4400	14m	2015

17. RECOVERY METHODS

The San Martin Mill is a conventional cyanidation mill using the Merrill Crowe recovery process, with a rated capacity of 1,100 tpd. The mill flowsheet employs two stage fine crushing, grinding is also two stages with both ball mills and a tower mill followed by total ore cyanide leaching in a CCD circuit. Gold and silver is recovered with zinc precipitation and is refined on site to doré.

In the period April 30, 2017 to April 30, 2018 the mill achieved an average throughput of 755 tpd with recoveries of 88 % for gold and 55 % for silver.

A tailings filtration plant to provide for dry handling and stacking of the tailings was installed in 2005 and the recommendations by AMEC have been implemented and the tailings dam is being reinforced to better standards. The San Martin flowsheet has been shown in previous section 13.

18. PROJECT INFRASTRUCTURE

SIM has all the necessary mine and mill infrastructure to operate the San Martin Mine Project efficiently and operates within all the regulatory standards imposed on the project by the various government agencies. Figure 18-1 is view of the portal of the San Martin Mine. Underground mine is relatively dry, no water pumping is necessary.



Figure 18- 1 Portal of the incline for the San Martin Mine

A great part of the facilities is occupied by the mill and tailings dam (Figure 18-2).

The installations in the mine site includes mine offices, maintenance shops, assays laboratory, warehouse and eating facilities for mine personnel (Figure 18-3). The mine and mill are

connected to the electric grid and the mine produces more than enough water for milling operations. Electrical power is supplied by the CFE in a power line of 34.5 kVa. A secondary electricity generating system with about 500kW capacity to supply power to the mill during a power failure and during the peak supply times when prices are higher, is available.



Figure 18- 2 Installations of mill at the San Marin Mine



Figure 18- 3 Office buildings for the mine. Operation of the furnace at the San Martin assay laboratory.

19. MARKET STUDIES AND CONTRACTS

The San Martin final product is a doré bar of clean product with few impurities. There are numerous refineries around the world available to refine the doré. Gold and silver doré in the form of bullion that is produced from the mines was shipped primarily to Itaipreziosi Precious Metals Refinery in Italy. Doré bars are paid at the gold and silver price established by London Fix at the time of the transaction.

20. ENVIRONMENTAL STUDIES, PERMITTING AND SOCIAL OR COMMUNITY IMPACT

20.1 General

The San Martin mine operates under the policy of zero industrial discharges into the environment. Surface water in the tailings disposal facilities practically zero due to the tailings are filtered before sending to the dam.

Running water in the intermittent streams within the property is tested for mineral elements and contaminants. Some water pumped from the underground workings is discharged in the water storage reservoir at the surface and used later for mineral processing. The following aspects are treated with special care by the company as they represent potential risks to the operation. To reduce the possibility of an incident regarding any of these issues, San Martin has established strict procedures of operation and monitoring in accordance with accepted standards.

- The tailing dams require strict environmental and operation control because the proximity to the San Martín community represents a risk.
- Testing for water pollutants into creeks near the tailings dams.
- Testing of discharge sewage pollutants.
- Testing of the combustion gases from laboratory's chimneys and foundry, and lead exposure for lab workers.

20.2 Permitting

Currently, SIM has maintained all the necessary permits for exploration and exploitation at the San Martín mine site (Table 20-1). A Manifestacion de Impacto Ambiental (MIA) was submitted to Secretaría de Medio Ambiente y Recursos Naturales (SEMARNAT) in April 2004. The license covers all related to the underground expansion of the mine. In March 2011 approval of a MIA by SEMARNAT allows an expansion for tailings facilities that were not previously required. An amendment for stabilization and expansion was approved by SEMARNAT in early August 2016. Tailings have been tested periodically, last test was in June 14, 2018. The results were presented by Intertek+ABC Analytic, finding all within normal parameters.

A mining concession in Mexico does not confer any ownership of surface rights. However, use of surface rights for exploration and production can be obtained under the terms of various acts and regulations if the concession is on government land. The San Martin concessions are located on Ejido (community or co-op) and private property land, and all the agreements with the surface owners has been signed which allows SIM access and authorization to complete exploration and mine operations activities.

Table 20- 1 List of permits of the San Martin Mine

Permit	Mining Stage	Agency	Status
Environmental Impact Statement (MIA)	Construction/operation abandonment	Secretary of Environmental and Natural Resources (SEMARNAT)	In place
Land use change study	Operation/ abandonment	SEMARNAT- General Department of Permitting for Forrestry and Soils	In place
Explosive handling and storage permit	Operation	National Secretary of Defense (SEDENA)	In place
Archeaological Release Letter	Operation	Nation Institute of Srcheology and History (INAH)	In place
Water use concession title	Operation	National Comission of Water (CNA)	In place
Water discharge permit	Operation	National Comission of Water (CNA)	In place
Surface Owners Agreement	Access, direct exploration and drilling	Surface owners	In place
Preventive Environmental Impact Report	Raod conditioning and direct exploration	Secretary of Environmental and Natural Resources (SEMARNAT)	In place

20.3 Tailings Dam and Reforestation

A reinforcing berm of compacted fill was built along the downstream toe of the tailings dam to increase the dam safety factor. The downstream side of the reinforcing berm has been constructed at a 2:1 slope. A trench has been excavated and a French drain system constructed on the downstream side of the dam to intercept seepage. The seepage is collected in a sump for recycle back to the mill. The French Drain trench has been backfilled and the area is being re-vegetated.

All the tailings dam construction follows recommendations made by AMEC who visit the site periodically to ensure that construction is adequate. A diversion ditch at the north end of the pond has been completed and all final berms are being re-constructed of compacted tails with waste rock rip-rap exteriors.

The reforestation, in the tailings dam, is done with 22 species of plants produced in the nursery of the mining unit, among shrubs, trees and herbaceous. First the preparation of the land is made placing a layer of inert material (mixture of soil and rock) and on this one layer of vegetal soil, to later make the plantation with a relation of 1 individual by each 2 m², 1 arboreal species for each 4 shrubs and / or herbaceous, taking place mainly in the months of July and August, when the rains have stabilized to obtain a higher percentage of plant development. The annual average of the reforestation is over 5000 plants (Figure 20-1).



Figure 20- 1 Reforestation on the NE side of the tailings dam at San Martín.

20.3 Social and Community Impact

SIM considers nearby communities as important stakeholders and, as such, the company pays special attention to their problems and requests for support. A good neighbor and open-door policy characterizes the relations with the communities inside and around the area of operations. A company representative interacts with the local authorities frequently.

According to the population and housing census of 2010, the inhabitants in the surrounding communities include 52,401 people living in the 5 locations. Women are 51.3% of the population. Table 20-2 presents population by gender in the communities, and shows the relationship of San Martín with them, whether directly or indirectly.

Table 20- 2 Neighboring community population at San Martín mine

Location	Relationship	Population		
		Total	Male	Female
San Martín	Directly	1430	705	725
Peña de Bernal	Directly	3750	1816	1934
Ajuchitlán	Directly	5483	2631	2852
Ezequiel Montes	Indirectly	34724	16373	18356
Colón	Indirectly	7014	3415	3598

The relationship with a community is indirect whenever it has a direct relationship with another mining company. Regardless of the indirect relationship with these communities, San Martín considers that it has a shared commitment with them.

San Martín has a policy of social responsibility based on community development. The tactic used to achieve this strategic principle is focused on:

- Education and Employability: Promoting learning opportunities ranging from basic education to technical skills and supporting the creation and development of small business that provide an economic alternative to mining related jobs.
- Infrastructure: Supporting construction, improvement or rehabilitation of community facilities, such as the Church, the playgrounds, or the roads.
- Health: In partnership with government institutions, SIM promote several health campaigns in the communities such as dental, vaccines, nutrition, pet control, and others.
- Sports: Also, in partnership with government institutions and NGOs, SIM supports summer camps for children and in the last two years has sponsored one of the main races that happen in Guanajuato.
- Environment: SIM runs different environmental campaigns in the communities, such as the recycling of electronics, the reuse of tires to rehabilitate recreational sites, reforestation initiatives, cleaning up campaigns, and others.
- Traditions and Culture: SIM supports throughout the year the different celebrations that happen in the community, such as the day of the miner, mother’s day, day of the death, children’s day, Christmas celebrations, and others. SIM responds to ongoing requests from the community.

In order to carry out social responsibility actions, San Martín has an internal procedure intended to channel the demands of the local communities, to assess their needs, to prioritize them, and to evaluate donations to be made to improve quality of life.

21. CAPITAL AND OPERATING COSTS

Capital and operating budgets are prepared for each calendar year for the mine by mine staff. These budgets are continuously reviewed against production to ensure profitability. For the first

quarter of 2018 operating year the average cost of production was US\$69.41 per tonne milled, including capital allowance. This cost includes all minesite administration. SMI has some additional admin costs for head office administration and these numbers are well documented in the company's financial statements which are filed quarterly on SEDAR.com.

22. ECONOMIC ANALYSIS

SMI currently has only one operating mine and no other active exploration projects therefore the best economic analysis of the operation can be reviewed in the financials filed by SMI. See quarterly and annual financial statements for SMI on SEDAR.com.

23. ADJACENT PROPERTIES

Exploraciones Mineras La Parreña, S.A. de C.V. (Peñoles) has a claim of 822 hectares, located on the Central-West part of the SIM's concessions. The name of the claim is Colón and is registered with the Title No. 237380. Peñoles also holds The Palmita claim, Title 237379, with an area of 99.97 hectares.

Another property is the San Judas Tadeo claim, Title No. 220535, covering 700 hectares. This property is private and has three owners, the main owner is Ciro Feregrino. This property is located to the northeast of the SIM's claims.

24. OTHER RELEVANT DATA AND INFORMATION

This report summarizes all data and information material to the San Martín Mine Project as of April 30, 2018. QP knows of no other relevant technical or other data or information that might materially impact the interpretations and conclusions presented herein, nor of any additional information necessary to make the report more understandable or not misleading.

25. INTERPRETATION AND CONCLUSIONS

25.1 Exploration

Mr. Enriquez has the following conclusions regarding the exploration efforts and potential for the San Martin Mine Project:

- Several areas within San Martin would benefit from additional drilling, as the current spacing is insufficient to adequately define the continuity of mineralization for prospective mining. Areas that would benefit from additional drilling to improve confidence in the estimation include Santa Elena NE and the Santa Elena SW, both with potential resources for the future of the mine.
- Other areas such as extensions of Cuerpo 28 and the widening of the San Martin structure orebodies within the existing mining operations and would benefit from additional drilling to expand known resources.

- QP notes that areas such as Santa Elena NE would benefit from better positioning of drill stations, as some of the drilling orientation in the current maps, will only touch the structure near the actual mine workings at level 10.

25.2 Resource Estimates

Mr. Enriquez is of the opinion that the Mineral Resource Estimate has been conducted in a manner consistent with industry best practices and that the data and information supporting the stated mineral resources is sufficient for declaration of Inferred classifications of resources. QP has not classified any of the resources in the Measured category due to some uncertainties regarding the data supporting the Mineral Resource Estimate.

These deficiencies include:

1) The lack of a historic QA/QC program, which has only been supported by a recent resampling and modern QA/QC program for channel samples and a limited number of holes. This will be required in order to achieve Measured resources which generally are supported by high resolution drilling or sampling data that feature consistently implemented and monitored QA/QC.

2) The lack of consistently-implemented down-hole surveys in the historic drilling. Although the survey data doesn't show significant deviations from planned orientations, it would be priority to have all holes surveyed.

25.3 Mineral Reserve Estimates

Mr. Enriquez is of the opinion that the Mineral Reserve Estimate has been conducted in a manner consistent with industry best practices and that the data and information supporting the stated mineral reserves is sufficient for declaration of Proven and Probable classifications of reserves. The San Martín mine is a producing operation with over 17 years of continuous operation. Recent production data was used as a primary source of information to validate or derive, as necessary, the relevant modifying factors used to convert Mineral Resources into Mineral Reserves. The initial production decision was not based on a feasibility study of Mineral Reserves demonstrating economic viability. There is an increased uncertainty and economic and technical risks of failure associated with this production decision. The production schedule associated with this reserve estimate results in mining until December 2018 at an average production of approximately 850 tpd. The tailings storage facility is big enough to support the production of LOM without problem.

26. RECOMMENDATIONS

Outside of the currently known reserve/resource, the mineral exploration potential for the San Martín Mine are very good. Parts of the known vein splays beyond the historically mined areas also represent good exploration targets for additional resource tonnage. The concession areas contain many veins and targets for exploration and the QP considers there to be reasonable potential of discovering new veins and extensions, besides those that are currently known. An exploration budget has been developed for 2018 and discussed in the following section.

26.1 Exploration Program

Exploration budgets for San Martín are approved for 8,000 meters of drilling during 2018. Table 26-1 summarizes the planned 2018 exploration budget for San Martín.

Table 26- 1 Drifting and drilling budget for 2018

Area	DDH Program 2018	
	Metres	Budget US\$
San Martín	3,600	\$ 285,102
San José	4,800	\$ 277,291
Cuerpo 29	400	\$ 36,776
Cuerpo 30	600	\$ 31,394
Cuerpo 31 Y 32	3,600	\$ 205,160
Total	13,000	\$ 835,723

Diamond drilling program will be carried out with rigs property of SIM. Drilling will be performed underground, with exception of a couple of holes recommended for the Santa Elena SW Extension.

26.2 Geology, Block Modeling, Mineral Resources and Reserve

QP recommends that the continuation of the conversion of all resources into reserves from 2D polygons-blocks be continued. During 2017, considerable progress was made in this regard. Additional modeling efforts should be made to define the mineralized brecciated areas as they have been an import source of economic material encountered in the current operation and could provide additional tonnage to support the mine plan.

Currently SMI utilizes the exploration drilling and chip and muck samples in their resource and reserve calculations. QP recommends that future efforts focus on constructing block models for resource and reserve reporting utilizing only the chip-channel samples from stopes and drifts as well as exploration and underground drilling results. This will help in keeping data densities consistent in each modeling effort and allow another level into the reconciliation process to compare modeling results.

Although the reconciliations conducted by SIM show good comparisons on planned values versus actual values, the reconciliation process should be improved to include the estimated tonnes and grade from the resource blocks. By comparing the LOM plan monthly to the plant production, the actual physical location of the material mined may be different in the plan versus the actual area that was mined. Due to the many faces that are mined during a day this can only be completed on an average monthly basis to account for the blending of this material at the mill. The monthly surveyed as mined areas should be created and saved monthly for reporting the modeled tonnes for each month.

The model predicted results versus actuals can then be used to determine if dilution factors need to be adjusted or perhaps the resource modeling parameters may require adjustment if there are

large variances. On a yearly basis, the mill production should be reconciled to the final doré shipments and resulting adjustment factors should be explained and reported.

As discussed before, there is potential to increase the classification of the estimated mineral resources to Measured status, and to expand the extents of mineralization of economic interest within the San Martin property. The project therefore warrants significant additional investment in exploration with the goals of: (i) increasing confidence in the existing resources, which are potentially amenable to continue underground mining; (ii) expanding the potential open-pit resource base at the Santa Elena SW; and (iii) testing the high-grade vein potential at depth on the possible structure of Santa Elena NE.

The author recommends a drilling program with an estimated total cost of US\$835,723 as outlined in Table 26.1. Prior to significant surface activities, specifically drilling, project-wide digital topography should be obtained (DTM).

Proposed drilling at surface to test the Santa Elena SW includes at least 1000 metres in 2018. This drilling should focus on testing extensions to previously defined mineralization with trenching, including anomalous-grade wide structure within lithologic sedimentary units beneath the porphyritic rhyolite.

Extensive specific-gravity testing should be undertaken on all core holes drilled and from underground.

Following completion of the proposed drilling underground and surface, an updated resource estimate should be completed.

As a critical part of the work program summarized above, QP recommends that CMPB undertake the following data capture and evaluation to improve confidence in the project database and, together with the proposed drilling, support the classifications of ore for future resource estimations:

- Digital electronic compilation of all comments on the drill logs concerning sample recovery, sample quality, difficult drilling conditions, the intersection of historical workings, all mineralised structures, etc.;
- Attempt to resolve questions remaining about the details of the historical drill holes, including the dates drilled, hole types, drilling methods, and companies responsible;
- Digital electronic compilation of historical down-hole deviation records, if they can be located;
- Digital electronic compilation of original assays sheets from ICP or AA;
- Continue to seek records that quantify the tonnages and grades of the various brecciated material types processed and their respective gold and silver recoveries, as such information could be pertinent to future potential processing of different materials;
- Digital electronic compilation of Assay's QA/QC data, which exist in paper form;
- Attempt to locate any check-assay results or other QA/QC data pertinent to the mine laboratory and compile digitally in a monthly base;

It is also important for CMPB to compile and evaluate geophysical and geochemical data that may exist in the historical records. Insights gained from such an evaluation may be applicable to further exploration drilling of the property.

Finally, it is recommended that CMPB carry out the underground mine workings and drilling and other work proposed above using a coordinate system compatible with modern-day surveying and GPS measuring devices. The local minegrid and all historical drill-collar

locations should be transformed to Universal Transverse Mercator (“UTM”) projection. This will facilitate the siting and surveying of new drill holes and will allow the integration and evaluation of regional and district geophysical data. It is the author’s opinion that the San Martin Mine is a project of merit and warrants the proposed program and level of expenditures outlined above.

27. REFERENCES

- Buchanan, L. J., 1981, Precious metal deposits associated with volcanic environments in the southwest, in Dickinson, W.R., and Payne, W.D., eds., Relations of Tectonics to Ore Deposits: Arizona Geological Society Digest, v. 14, p. 237-262.
- Burk, R., 1993, Regional Geology of San Martín Property and Its Relationship to Precious Metal Mineralization, Central Queretaro State, Mexico. Priv. Rep. for Teck Cominco. MEXICO.
- Campbell, J., 2012, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2012. For Starcore International Mines LTD.
- Enriquez, E., 2003, Transformation of Resources into Reserves in Mining Operations of Luismin. An Update. Priv. Internal Report for Luismin. 30 p.
- Enriquez, E., 1995, Trace element zonation and temperature controls of the Tayoltita Ag-Au fossil hydrothermal system, San Dimas district, Durango, Mexico: Unpublished M. Sc. Thesis, Colorado School of Mines, 195 p.
- Gunning, D. R. and Campbell, J., 2011, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2011. For Starcore International Mines LTD.
- Gunning, D. R. and Campbell, J., 2014, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2014. For Starcore International Mines LTD.
- Gunning, D. R. and Whiting, B., 2009, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2009. For Starcore International Mines LTD.
- Gunning, D. R., 2013, Reserves and Resources in the San Martín Mine, Mexico, as of July 31, 2013. For Starcore International Mines LTD.
- Labarthe-Hernández, G. y Tristán-González, M., 2006, Geología del distrito minero de San Martín. Instituto de Geología de La UNAM. Rep. Priv. Compañía Minera Peña de Bernal, SA de CV., 44 p.
- Muñoz-Cabral, F., 1993, Modelo genético de los depósitos de oro proyecto San Martín, Qro., Asociación de Ingenieros de Minas, Metalurgistas y Geólogos de México, A.C., XX convención AIMMGM, octubre 27-30, 1993, Acapulco, Gro. México, p. 246-260
- Núñez-Miranda, A., 2007, Inclusiones Fluidas y Metalogénia del Depósito Epitermal Ag-Au del Distrito de San Martín, Mpio. Colón, Qro. MSc Thesis, 166p.
- Ortiz, H.L.E., Solís P.G.N., Mérida, C.A. 1989, Geología y metalogénesis del yacimiento auroargentífero-brechoide epitermal (tipo carlin) de San Martín, Querétaro. XVIII Convención Nacional de la A.I.M.M.G.M., A.C., p. 42-62.
- Rankin, L. R., 2008, Structural Controls on the Carbonate Breccia Hosted Au-Ag Mineralisation, San Martín Deposit, Central Mexico. Private internal report for Starcore International Mines LTD, 55 p.
- SGM Servicio Geológico Mexicano www.sgm.gob.mx
- Spring, V. and McFarlane, G.R., 2002, A Technical Review of the Tayoltita, Santa Rita, San Antonio, La Guitarra and San Martín Operating Silver and Gold Mines in Mexico. Watts, Griffis and McOuat NI 43-101 report prepared for Wheaton River Minerals Ltd.
- Spring, V., McFarlane, G.R. and Watts, G., 2004, A Technical Review of the Tayoltita, Santa Rita, San Antonio, and San Martín Mines. Watts, Griffis and McOuat NI 43-101 report prepared for Chap Mercantile Inc.
- Wisser, E. 1966, The Epithermal Precious-Metal Province of Northwest Mexico: Nevada Bureau of Mines Bulletin 13, part C, p. 63-92.

CERTIFICATE


To Accompany the Report titled

“Reserves and Resources in the San Martín Mine, Querétaro State, Mexico, as of April 30, 2018” for Starcore International Mines Ltd. dated June 30, 2018

I, Erme Enriquez, CPG of Alhelí 142, Fracc. Jardines de Durango, Durango, Dgo. Mexico hereby certify that:

1. I am currently an independent consulting geologist.
2. I am a graduate of the Universidad de Sonora having obtained the degree of BSc in 1983 and from Colorado School of Mines obtained the degree of MSc in 1996, both in Geological Engineering.
3. I have been employed in the mining industry continuously since 1983. Since 1985 I have performed resource and reserve estimating in several commodities, including extensive experience in gold and silver and base metals deposits.
4. I am a member of the American Institute of Professional Geologists of United States and use the title of CPG (Certified Professional Geologist). I am also a Fellow of the Society of Economic Geologists (SEG) and a member La Asociación de Ingenieros de Minas Metalurgistas y Geólogos de México (AIMMGM).
5. I have read the definition of “Qualified Person” set out in National Instrument 43-101(NI 43-101) and certify that by reason of my education, affiliation of my professional association and past relevant work experience, I fulfil the requirements to be a “Qualified Person” for the purposes of NI 43-101.
6. I have read the definition of “Independence” set out in NI 43-101 and certify that I do not fulfil the requirements of “Independence” for the purposes of NI 43-101.
7. I have been a reviewer of previous reserve reports on the San Martín Mine from 1998 to 2002 for Minas Luismin, SA de CV.
8. I have visited the San Martín Mine from June 12 to 15 of 2018.
9. I am not aware of any material fact or material change with respect to the subject matter of the Technical Report that is not reflected in the Technical Report, the omission to disclose which makes the Technical Report misleading.
10. I have read the instrument and Form 43-101F. The Technical Report titled **“Reserves and Resources in the San Martín Mine, Querétaro State, Mexico, as of April 30, 2018”**, which was prepared from information available as of April 30, 2018, and has been prepared in compliance with the instrument and form. I am responsible for this report.
11. I consent to the filing of the Technical Report with and stock exchange and other regulatory authority and any publication by them, including electronic publication in the public company files on their websites accessible by the public, of the Technical Report.

Dated this 27th day June 2018

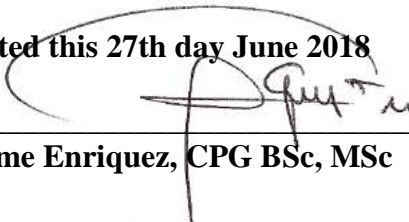
Erme Enriquez, CPG BSc, MSc



APPENDIX I
RESERVE BLOCKS BY MINE AREA

**SAN MARTIN MINE
SAN JOSÉ AREA**

RESEVAS PROBADAS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SJII4046-1	28608	3.25	1.66	4	1.71	1574
SJII4253-1	11322	4.17	1.70	6	1.77	643
SJII549-1A	2807	1.73	1.50	8	1.60	144
SJII4060-1	2444	1.24	1.80	10	1.92	151
SJII560-1	8816	2.39	1.46	20	1.70	483
SJII650-1	4616	2.28	2.47	25	2.78	412
SJII650-2	4555	2.29	2.46	25	2.77	405
SJII549-1	4728	3.12	1.51	13	1.67	253
SJII4095-1	2744	2.02	2.24	6	2.32	204
SJII4060-2	4365	2.21	1.99	8	2.08	292
SJII 418-1	1739	2.37	1.70	6	1.78	99
SJII 549-2	3584	1.67	1.74	11	1.87	216
SJII 655-2	6156	2.72	1.76	10	1.89	373
0	0	0.00	0.00	0	0.00	0
	86,485	2.85	1.77	10	2	5,252
RESERVAS PROBABLES DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SJII549-3	6375	3.12	1.51	13	1.67	342
SJII549-3A	4668	1.62	1.60	8	1.69	254
SJII650-3	4854	2.39	2.39	24	2.69	420
SJII 418-2	1326	2.37	1.70	6	1.78	76
SJII 549-4	3677	1.63	1.78	11	1.91	226
SJII 655-4	6523	2.72	1.76	10	1.89	395
0	0	0.00	0.00	0	0.00	0
0	0	0.00	0.00	0	0.00	0
	27,425	2.40	1.78	13	2	1713
ROBADAS + PROBABLE	113,910	2.75	1.77	11	2	6,965
RECURSOS INFERIDOS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SJII Inf 01	160498	2.77	1.87	11	2.00	10317
	160,498	2.77	1.87	11	2	10317
	274,408	3.10	2.05	12	2.20	17,282

**SAN MARTIN MINE
SAN MARTÍN AREA**

RESEVAS PROBADAS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SM 10400-1	27893	2.73	2.00	9	2.11	1889
	27,893	2.73	2.00	9	2	1,889
RESERVAS PROBABLES DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SM BDD 01	569618	4.21	1.92	11	2.06	37721
GP 12000 C-1	465649	3.44	1.76	16	1.96	29305
						0
						0
						0
						0
						0
	1,035,267	3.86	1.85	13	2	67026
PROBADAS + PROBABLES	1,063,160	3.83	1.86	13	2	68,915
RECURSOS INFERIDOS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
SM Inf 01	454288	3.81	1.82	11	1.95	28453
GP Inf 02	410400	3.44	1.76	16	1.96	25828
	864,688	3.63	1.79	13	2	54281
	1,927,848	4.37	2.13	15	2.32	123,196

**SAN MARTIN MINE
CUERPO 28 AREA**

RESEVAS PROBADAS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
28 1103-1	9487	3.65	2.21	5	2.26	690
28 1103-2	5563	1.83	2.66	4	2.70	484
28 1103-3	10462	1.71	2.19	3	2.23	750
28 4058-1	1427	1.91	1.77	36	2.22	102
28 4058-2	1553	1.91	1.77	36	2.22	111
28 2060-1	105093	4.50	2.44	88	3.52	11889
28 2062-1	87680	2.86	1.93	89	3.02	8520
	221,265	3.58	2.21	78	3	22,545
RESERVAS PROBABLES DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
28 4058-3	1520	1.91	1.77	36	2.22	108
28 4058-4	1520	1.91	1.77	36	2.22	108
28 2060-2	49511	5.40	2.44	88	3.52	5601
28 2062-2	97763	4.50	1.93	89	3.02	9500
	150,314	4.74	2.09	88	3	15318
PROBADAS + PROBABLES	371,579	4.05	2.16	82	3	37,863
RECURSOS INFERIDOS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
28 Inf 01	182684	4.79	2.44	88	3.52	20666
4700 Inf 02	92918	1.91	1.77	36	2.22	6625
	275,602	3.82	2.22	70	3	27292
	647,181	4.65	2.56	91	3.68	65,155

**SAN MARTIN MINE
CUERPO 30 AREA**

RESEVAS PROBADAS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
30 6107-1	5464	1.42	1.35	30	1.73	303
30 6155-1	987	3.30	1.94	17	2.14	68
5939-1	3168	3.45	17.12	56	17.81	1814
						0
						0
	9,618	2.28	6.60	38	7	2,185

**SAN MARTIN MINE
CUERPO 31 AREA**

RESEVAS PROBADAS DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
318723-1	3646	2.08	4.05	32	4.44	520
318723-2	3348	2.08	4.05	32	4.44	478
313185-2	1270	2.61	3.94	18	4.17	170
	8,264	2.16	4.03	30	4	1,168

RESERVAS PROBABLES DILUCION (20%)						
Block	Tons Diluidas	Ancho (m) Diluido	Au	Ag	AuEq	Onzas Totales
313185-3	1211	2.45	5.93	41	6.43	251
313185-4	9511	2.45	5.93	41	6.43	1967
	10,722	2.45	5.93	41	6	2218
PROBADAS + PROBABLES	18,986	2.32	5.10	36	6	3,385